OFFICE OF NAVAL RESEARCH

AD-A267 318

Contract N00014-89-J-1028

Technical Report No. 18

# Photochemistry of Bisphenol-A Based Polycarbonate: Early Detection of Photoproducts by Fluorescence Spectroscopy

by

C.E. Hoyle, H. Shah, and I.B. Rufus

Prepared for Publication in

Macromolecules

Department of Polymer Science
University of Southern Mississippi
Hattiesburg, MS 39406-0076

DTIC
ELECTE
JUL 30 1993
S B D

Reproduction in whole or in part is permitted for any purpose of the United States government.

This document has been approved for public release and sale: its distribution is unlimited.

93-16994

SECURITY CLASSIFICATION OF THIS PAGE

# REPORT DOCUMENTATION PAGE

| | |
|---|---|
| 1a. REPORT SECURITY CLASSIFICATION<br>NONE | 1b. RESTRICTIVE MARKINGS<br>NONE |
| 2a. SECURITY CLASSIFICATION AUTHORITY<br>NONE | 3. DISTRIBUTION/AVAILABILITY OF REPORT<br>UNLIMITED |
| 2b. DECLASSIFICATION/DOWNGRADING SCHEDULE<br>NONE | |
| 4. PERFORMING ORGANIZATION REPORT NUMBER(S)<br>TR #18 | 5. MONITORING ORGANIZATION REPORT NUMBER(S)<br>ONR N0014-89-J-1028 |
| 6a. NAME OF PERFORMING ORGANIZATION<br>University of Southern Mississippi<br>6b. OFFICE SYMBOL (If applicable) | 7a. NAME OF MONITORING ORGANIZATION<br>Office of Naval Research |
| 6c. ADDRESS (City, State, and ZIP Code)<br>University of Southern Mississippi<br>Polymer Science Department<br>Southern Station Box 10076<br>Hattiesburg, MS 39406-0076 | 7b. ADDRESS (City, State, and ZIP Code)<br>800 North Quincy Avenue<br>Arlington, VA 22217 |
| 8a. NAME OF FUNDING/SPONSORING ORGANIZATION<br>Office of Naval Research<br>8b. OFFICE SYMBOL (If applicable) | 9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER |
| 8c. ADDRESS (City, State, and ZIP Code)<br>800 N. Quincy Avenue<br>Arlington , VA 22217 | 10. SOURCE OF FUNDING NUMBERS<br>PROGRAM ELEMENT NO. / PROJECT NO. / TASK NO. / WORK UNIT ACCESSION NO. |

11. TITLE (Include Security Classification)

Photochemistry of Bisphenol-A Based Polycarbonate: Early Detection of Photoproducts by Fluorescence Spectroscopy

12. PERSONAL AUTHOR(S)

C.E. Hoyle, H. Shah and I.B. Rufus

| 13a. TYPE OF REPORT | 13b. TIME COVERED | 14. DATE OF REPORT (Year, Month, Day) | 15. PAGE COUNT |
|---|---|---|---|
| Technical | FROM 6/1/91 TO Present | 93/7/13 | |

16. SUPPLEMENTARY NOTATION

Submitted for publication in Macromolecules.

| 17. COSATI CODES | | | 18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number) |
|---|---|---|---|
| FIELD | GROUP | SUB-GROUP | |
| | | | |
| | | | |

19. ABSTRACT (Continue on reverse if necessary and identify by block number)

The utility of fluorescence spectroscopy in detection of salicylic acid and 2,2'-biphenol type products in the very early stages of photolysis of polycarbonate and its model compounds has been demonstrated. The broad structureless peak around 410 nm produced by photolysis of polycarbonate and model compounds in THF is assigned to emission from a salicylic acid type photoproduct. Formation of salicylic acid has been shown to be dependent on the presence of oxygen. The emission with peak maximum around 360 nm produced by photolysis of polycarbonate and model compounds in THF (or dichloromethane) is consistent with fluorescence from a 2,2'-biphenol type photoproduct. Salicylic acid and 2,2'-biphenol are quite photolabile, hence the need for their early detection during photolysis of polycarbonate.

| 20. DISTRIBUTION/AVAILABILITY OF ABSTRACT | 21. ABSTRACT SECURITY CLASSIFICATION |
|---|---|
| ☒ UNCLASSIFIED/UNLIMITED ☒ SAME AS RPT. ☐ DTIC USERS | |
| 22a. NAME OF RESPONSIBLE INDIVIDUAL<br>C.E. Hoyle | 22b. TELEPHONE (Include Area Code)<br>(601)266-4868 / 22c. OFFICE SYMBOL |

DD FORM 1473, 84 MAR 83 APR edition may be used until exhausted. All other editions are obsolete.

SECURITY CLASSIFICATION OF THIS PAGE

# Photochemistry of Bisphenol-A Based Polycarbonate: Early Detection of Photoproducts by Fluorescence Spectroscopy.

**Himanshu Shah, Isaac B. Rufus, and Charles E. Hoyle***

Department of Polymer Science, University of Southern Mississippi,

Hattiesburg, Mississippi 39406-0076.

## ABSTRACT

The utility of fluorescence spectroscopy in detection of salicylic acid and 2,2'-biphenol type products in the very early stages of photolysis of polycarbonate and its model compounds has been demonstrated. The broad structureless peak around 410 nm produced by photolysis of polycarbonate and model compounds in THF is assigned to emission from a salicylic acid type photoproduct. Formation of salicylic acid has been shown to be dependent on the presence of oxygen. The emission with peak maximum around 360 nm produced by photolysis of polycarbonate and model compounds in THF (or dichloromethane) is consistent with fluorescence from a 2,2'-biphenol type photoproduct. Salicylic acid and 2,2'-biphenol are quite photolabile, hence the need for their early detection during photolysis of polycarbonate.

## Introduction

Polycarbonate is an important engineering thermoplastic possessing a variety of useful properties including optical clarity, high impact strength, and high percent

---

* To whom all correspondence should be addressed.

elongation. However upon natural weathering, these and other properties deteriorate rapidly[1,2]. As a result, the photodecomposition of bisphenol-A based polycarbonate has been studied by several research groups over the last three decades[3-23]. A review of the literature indicates two possible pathways for the photodecomposition of bisphenol-A based polycarbonate viz. α-cleavage of the carbonyl carbon-oxygen bond and photo-oxidation. Photo-Fries rearrangement resulting from the α-cleavage process (Scheme I) has been reported to occur upon direct absorption of light by the diaryl carbonate repeat units. Photo-oxidation has also been reported from photolysis of impurities[11]. Our focus in this paper will be on the primary oxygen-carbonyl carbon bond cleavage and the resultant recombination products. We will demonstrate that these products are produced efficiently in the very early stages of photolysis.

The initial photo-Fries rearrangement of polycarbonate occurs via a radical cage mechanism (Scheme I): Rivaton and coworkers[16,18] have proposed that the phenyl salicylate and the 2,2'-dihydroxybenzophenone type photoproducts (formed by photo-Fries rearrangements) can undergo further photolysis in the presence of oxygen to give acid groups (based on IR absorbance at 1713 $cm^{-1}$). It has also been suggested that initial expulsion of carbon monoxide and carbon dioxide from the radical cage followed by recombination of the resultant radicals can lead to a variety of coupling products[6,7,14,15,16,20,24,25] (refer Scheme II). In this paper we report detection of the 2,2'-biphenolic coupling product during the very early stages of photolysis of polycarbonate, in addition to phenyl salicylate and salicylic acid type products, using fluorescence spectroscopy. Identification of these photoproducts is important since it gives us insight



DTIC QUALITY INSPECTED 3

Avail and/or
Special
A-1

into the decomposition mechanism of polycarbonate, and leaves little question as to the role of such processes during the very early stages of polycarbonate photolysis. Fluorescent photoproducts are formed even in sunlight as we will briefly describe at the end of the paper. Our results are of particular interest in view of the observation that Factor *et. al.*[20] made in their latest paper concerning the presence of photo-Fries products upon long term exposure of polycarbonate to sunlight.

**Experimental**

Diphenyl carbonate (99% Polyscience) was recrystallized from methanol. Phenyl salicylate (99%, Aldrich) was recrystallized from methanol. Two different samples of polycarbonate (from General Electric) were used during the course of this investigation. The first (designated as sample A) was a FDA grade sample with at least some processing history. The second (sample B) was a Lexan® 140 polycarbonate sample with no prior thermal history. Spectral results of our interest did not depend upon the sample which was used. However, for completeness we note that Sample A was used to obtain data in Figures 9a and 9b while sample B was used to obtain data in other figures. Bis(phenyl carbonate) of bisphenol-A was synthesized and purified using procedure reported by Humphrey and co-workers[7]. Spectral grade dichloromethane (DCM) and tetrahydrofuran (THF) from Burdick & Jackson were used. Polycarbonate films were cast from approximately 10 wt% solution in dichloromethane.

Salicylic acid (99+ %), phenol (redistilled, 99+ %), diphenyl ether (99%), 2-phenyl phenol (99+ %), 4,4'-biphenol (99+ %, zone refined) and tert-butyl phenol (99%) obtained from Aldrich were used without further purification. 4-Hydroxy benzoic acid phenyl ester

(TCI America) was purified by reprecipitation from water/methanol mixture. Phenyl formate (95%, Lancaster) was vacuum distilled. 2,2'-biphenol (99%, Aldrich) was purified by vacuum sublimation.

Photolysis was carried out in air (unless otherwise mentioned) in a Rayonet Reactor with lamps having a maximum of about 300 nm. UV spectra were obtained on a Perkin-Elmer Lambda 6 UV-Vis spectrophotometer and fluorescence spectra were obtained on a SPEX Fluorolog-2. Chromatographic analysis of the samples was performed on a Hewlett Packard 5890 gas chromatograph. High performance liquid chromatographic analysis was performed on a Waters system (Model 6000A solvent delivery pump) with either a UV detector (Lambda Max Model 481, Waters) or fluorescence detector (Model 650 S from Perkin Elmer).

**Results and Discussion**

In a previous paper[26] we showed that it was possible to use fluorescence spectroscopy to identify photoproducts during the very early stages of polycarbonate photolysis. We indicated that photoproducts could be identified via characteristic fluorescence emission, according to peaks having maxima at about 470-480 nm in dichloromethane. In this paper, we employ fluorescence spectroscopy to identify the formation of biphenolic and salicylic acid type products produced during photolysis of both appropriate model compounds and polycarbonate. The salicylic acid chromophores are formed as a result of the secondary photolysis of phenyl salicylate photoproducts which themselves are generated in the initial photolysis step. In our previous analysis[26], we had assigned an emission with maximum around 470 nm produced upon photolysis

of both polycarbonate and diphenyl carbonate to a photo-Fries product, produced according to the simple pathway in Scheme I. Interestingly, this original analysis was performed upon samples in dichloromethane, a solvent in which both phenyl salicylate and salicylic acid have similar fluorescence emission and excitation energy maxima (470 nm for phenyl salicylate and 460 nm for salicylic acid). This did not allow for their absolute differentiation (see Figure 1). In the ensuing discussion, we will describe a procedure which allows for detection via fluorescence spectroscopy of salicylic acid as well as phenyl salicylate. By application of this analysis technique to photolyzed solutions of diphenyl carbonate and polycarbonate, we will demonstrate that both products are indeed formed during the early stages of exposure (short photolysis times). By careful extension to polycarbonate films, the production of salicylic acid type products during the initial stages of polycarbonate photolysis will be established. In addition, we will also utilize fluorescence spectroscopy to show that the 2,2'-biphenolic product, which one might deduce would form based on Rivaton *et. al.*[14,16] papers, is indeed generated in the very early stages of polycarbonate photolysis. Implications of the detection of fluorescent photoproducts upon photolysis of polycarbonate films in sunlight will be briefly touched upon in a prelude to a full paper which will describe the photolysis of polycarbonate at wavelengths corresponding to those comprising sunlight.

**A. Model Compound Photolysis**

Figure 2 shows emission and excitation spectra ($\lambda_{EX}$ = 310 nm) for diphenyl carbonate in dichloromethane (DCM) and tetrahydrofuran (THF). Diphenyl carbonate does not absorb at wavelengths greater than 280 nm, and hence when excited at 310 nm

(before photolysis), no fluorescence is observed in either DCM or THF. Upon photolysis, fluorescence bands with maxima around 360 nm and 470 nm in DCM and 360 nm and 410 nm in THF develop upon excitation at 310 nm. Why the large difference between results in DCM and THF: Is it a result of different products being formed in THF and DCM, or do the photoproducts fluoresce at different wavelengths in the two solvents? In Figure 3, the fluorescence spectra of phenyl salicylate and salicylic acid in THF are provided for comparison with the results in Figure 1. A cursory examination reveals that while phenyl salicylate shows little difference in the fluorescence emission maxima in DCM (470 nm) and THF (465 nm), salicylic acid has an emission maximum which is markedly blue shifted in THF (410 nm) compared to DCM (460 nm). The blue shift in THF results from a disruption in the internal hydrogen bonding of salicylic acid by the ether functionality of THF[27]. This remarkable blue shift in THF for salicylic acid does not occur for phenyl salicylate. Hence, we have a convenient method for differentiating between emission from salicylic acid and phenyl salicylate. This blue shift for salicylic acid in THF is accompanied by about a twenty fold increase in the fluorescence intensity, hence making fluorescence analysis in THF extremely sensitive for early detection of salicylic acid. By comparison of the photolysis results for diphenyl carbonate in THF (Figure 2b) with the blue shifted emission for salicylic acid in THF in Figure 3a, one can postulate that indeed photolysis of diphenyl carbonate in THF leads to the eventual formation of salicylic acid, no doubt via the photolysis of phenyl salicylate (the primary photolysis product of diphenyl carbonate). The presence of both phenyl salicylate and salicylic acid upon photolysis of diphenyl carbonate in THF is confirmed by HPLC retention times of the diphenyl

carbonate photolyzed reaction mixture with authentic samples of phenyl salicylate and salicylic acid. We note that HPLC identification of phenyl salicylate and salicylic acid is facilitated by analysis of a photolyzed sample at very short photolysis times before phenyl salicylate and salicylic acid themselves are consumed by photolysis. In other words, the steady state concentrations of phenyl salicylate and salicylic acid are quite small for photolysis of diphenyl carbonate with a lamp source such as the 300 nm (broad emission centered at 300 nm) Rayonet lamps used in this study.

Before completing our discussion of the method for determination of salicylic acid in photolyzed solutions of diphenyl carbonate, we should point out that identification of the precursor phenyl salicylate can be facilitated by recording excitation spectra of photolyzed THF solutions of DPC at several emission wavelengths. Since the fluorescence of phenyl salicylate is red shifted by about 50 nm from salicylic acid, excitation spectra recorded for emission monochromator settings greater than 450 nm should show a larger contribution from the phenyl salicylate component (if present) than excitation spectra obtained corresponding to emission monochromator settings at 410 nm, where the contribution to the total fluorescence intensity is dominated by salicylic acid. The shift expected in the excitation spectrum of the photolyzed DPC solution is a direct result of $\approx$ 10 nm blue shift in the excitation spectrum of pure salicylic acid in THF compared to phenyl salicylate in THF (Figure 3b). Figure 4 shows excitation spectra recorded for a diphenyl carbonate solution in THF photolyzed for 3 min. The blue shift in the excitation spectrum recorded for emission at 400 nm (compared to the spectrum recorded for emission at 470 nm) indicates that both phenyl salicylate and salicylic acid are present:

We note that, as described earlier, this is exactly the results obtained by HPLC analysis of the photolyzed solution. Incidentally, although not shown herein, independently prepared solutions of phenyl salicylate and salicylic acid exhibited no wavelength dependency for the excitation spectra. Hence, based on a combination of emission and excitation spectra, it is possible to identify the formation of both salicylic acid and phenyl salicylate products formed in the early stages of photolysis of diphenyl carbonate.

In order to clarify the origin of the salicylic acid and verify that it is indeed formed upon photolysis of the photo-Fries product phenyl salicylate, independently prepared solutions of phenyl salicylate in DCM and THF were subjected to the identical photolysis conditions employed for the diphenyl carbonate photolysis. In both cases, HPLC, GC and fluorescence analysis (Figures 5 and 6) indicate the formation of salicylic acid after short photolysis times. In THF, as would be expected by examination of the fluorescence from phenyl salicylate and salicylic acid in Figures 1a and 3a, the shift in the fluorescence maximum with photolysis time from 460 nm to 410 nm is dramatic while in DCM it is rather modest. The large increase in overall fluorescence intensity in THF compared to DCM is a result of the much higher fluorescence quantum yield (about 20 times greater) for salicylic acid in THF. The generation of salicylic acid upon photolysis of phenyl salicylate in both protic and non-protic solvent was reported over two decades ago[28]. Our present analysis not only serves to reiterate this important point, but also establishes the utilization of fluorescence spectroscopy as an analysis tool for detection of salicylic acid in the very early stages of phenyl salicylate photolysis. Use of fluorescence as an analysis method will be shown to be an invaluable method for investigation of polycarbonate film

photolysis. It is the difference in the fluorescence emission maximum in DCM and THF which will be utilized for identification of salicylic acid type chromophores upon photolysis of polycarbonate films.

Before turning to an analysis of polycarbonate film photolysis, we want to consider the photolysis of another model compound for polycarbonate, i.e., the bis(phenyl carbonate) of bisphenol-A (see structure below).

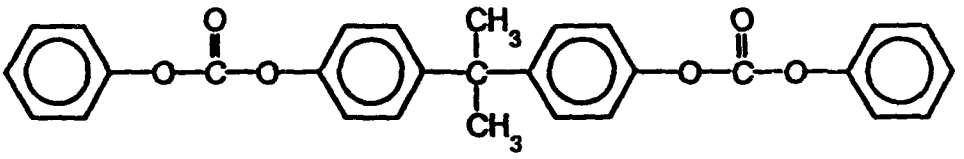

**Bis(Phenyl Carbonate) of Bisphenol-A**

Figure 7a shows the emission spectra of the model recorded at short photolysis times (Rayonet reactor, 300 nm lamps) in THF. The emission maximum at 410 nm corresponds to a salicylic acid type product. Figure 7b shows the excitation spectra($\lambda_{EM}$ = 400 and 470 nm) for the model compound in THF after photolysis at 300 nm for 3 min. The excitation spectra maxima for emission at 400 nm (near salicylic acid maximum) are blue shifted compared to the excitation spectra recorded for emission at 470 nm where the emission is primarily from phenyl salicylate. Hence, we conclude from the results in Figures 7a and 7b for the more exacting (compared to DPC) model for polycarbonate that photolysis leads to the formation of salicylic acid in the very early stages of photolysis.

One last consideration must be given attention to prior to presenting the fluorescence analysis results for polycarbonate. Figures 2a, 2b, and 7a clearly show the presence of a prominent second peak (well below 400 nm) in the fluorescence spectra of the photolyzed DPC and polycarbonate model compounds. In order to provide a reasonable explanation for the appearance of this peak at such short photolysis times, a large number of potential photoproducts[6,7,14,15,16,20,24,25] were screened for their fluorescence spectral characteristics: Table I provides a listing of fluorescence emission and UV-visible absorption maxima in DCM of these compounds. Only 2,2'-biphenol and 4,4'-biphenol have emission maxima above 340 nm. During photolysis of DPC, one would expect formation of all isomers of biphenols viz. 2,2', 4,4', and 2,4'-biphenols. However during photolysis of polycarbonate and bis(phenyl carbonate) of bisphenol-A, since the para positions to carbonate group are blocked, only the 2,2'-biphenol type product can be formed. The emission spectrum (excitation at 310 nm) of 2,2'-biphenol in THF is shown in Figure 8. The resemblance of the spectrum in Figure 8 for 2,2'-biphenol and the spectrum of the photolyzed model in Figure 7a is striking suggesting that 2,2'-biphenol, in addition to phenyl salicylate and salicylic acid type products, is produced upon photolysis at short times [The peak in Figures 2a, 2b, 7a and 8 at wavelengths slightly less than 350 nm is due to a solvent scattering resulting from excitation at 310 nm: The real maxima of 2,2'-biphenolic compounds in all those spectra are at about 360 nm]. This result is consistent with expulsion of carbon monoxide from the aryl formoxyl radical species, generated by the initial $\alpha$-cleavage of the oxygen/carbonyl carbon bond, and recombination with the corresponding aryloxy group in the solvent cage before diffusion

occurs (refer Scheme II). Such aryloxy coupling products were indeed suggested by previous investigation of polycarbonate[14,16] as well as a model system[6,24]. Furthermore, Horspool and Pauson[25] had reported that traces of di-tertbutyl diphenol coupling products were obtained upon photolysis of appropriate diaryl carbonate models in solution. We also find evidence via HPLC analysis and comparison with an appropriate authentic sample for the formation of 2,2'-biphenol and 4,4'-biphenol upon photolysis of DPC in DCM or THF at 254 nm. Due to lack of authentic sample, formation of the 2,4'-biphenol isomer during photolysis of DPC in DCM (or THF) could not be confirmed even though the HPLC analysis exhibited a peak where we would expect 2,4'-biphenol to appear. It is intuitively obvious that biphenolic coupling products should be formed for polycarbonate photolysis since there is a significant expulsion of carbon monoxide from polycarbonate films upon exposure to light[4,11,20]. Having established a viable tool, i.e., fluorescence spectroscopy, for detection of biphenolic type products, it is now possible to analyze films of polycarbonate photolyzed at very short times for the presence of biphenolic type products, as well as the phenyl salicylate and salicylic acid derivatives already discussed.

**B. Polycarbonate Photolysis**

Separation and identification of the photoproducts formed during the photolysis of any polymer, including polycarbonate, is extremely difficult. However, comparison of the fluorescence results for the photolysis of the model compounds and the polycarbonate (conducted under the same conditions) can give us a fairly reliable analysis for the types of photoproducts formed. We begin by solution photolysis of polycarbonate before extension to films. We had previously shown that photolysis of polycarbonate in DCM

resulted in an increase in the fluorescence emission spectrum with a maximum around 470 nm[26]. This red-shifted fluorescence is due to phenyl salicylate and salicylic acid type photoproducts: The presence of both phenyl salicylate ($\lambda_{max}$ = 470 nm in DCM) and salicylic acid ($\lambda_{max}$ = 460 nm in DCM) is difficult to specify by just recording the emission spectrum in DCM as discussed previously in this paper for the model system photolysis. However, by recording the excitation spectra of the photolyzed polycarbonate solution in THF at different wavelengths between 400 and 500 nm, the presence of two species i.e. phenyl salicylate and salicylic acid can be inferred. Hence, of particular interest are the excitation and emission spectra ($\lambda_{EX}$ = 310 nm) for photolyzed polycarbonate in THF (Figures 9a and 9b). The fluorescence buildup around 410 nm (Figure 9a) is similar to that observed for the photolysis of the BPA based model in THF (Figure 7a), photolysis of diphenyl carbonate in THF (Figure 2b) and the photolysis of phenyl salicylate in THF (Figure 6): All match the emission maximum for salicylic acid in THF (Figure 3a). The peak maxima for the photolyzed polycarbonate in THF occurring near 300 nm in the excitation spectra ($\lambda_{EM}$ = 410 nm, Figure 9b) is also quite consistent with the formation of a salicylic acid type photoproduct. The peak with maximum around 360 nm for the photolyzed polycarbonate in THF, by comparison with the spectrum in Figure 8, is indicative of formation of biphenolic type photoproducts at short photolysis times. Excitation spectra (Figure 10) obtained for photolyzed polycarbonate in THF (3 min sample) for emission at 470 nm (phenyl salicylate and salicylic acid type products), 400 nm (salicylic acid type product), and 370 nm (biphenolic type product) show the progressive shift of the excitation maxima to high energies (blue shift) expected for fluorescence corresponding

to the presence of multiple chromophoric groups as listed in parentheses.

Extending our analysis to polycarbonate films, Figure 11 shows emission spectra ($\lambda_{EX}$ = 325 nm) for the polycarbonate film in air before and after photolysis. As for the model compounds and polycarbonate in THF, the fluorescence maxima for the photolyzed film are observed about 360 nm and 470 nm [Note the absence of the solvent scatter peak maximum just less than 350 nm which occurs for the spectra in DCM or THF in Figures 2a, 2b, 7a, 8 and 9a]. The fluorescence buildup around 360 nm is strikingly similar to that for the photolysis of DPC (Figure 2b), the model compound (Figure 7a) and polycarbonate in DCM (not shown) and THF (Figure 9a). The fluorescence buildup around 450-500 nm is broad and could be due to phenyl salicylate and/or salicylic acid type photoproducts. To establish the species responsible for the emission from 450-500 nm, photolyzed polycarbonate films were dissolved in DCM and in THF. Figures 12a and 12b show the emission spectra ($\lambda_{EX}$ = 310 nm) for the photolyzed film dissolved in DCM and THF, respectively. The distinct red shift in the maximum for 470 nm in DCM to 410 nm in THF clearly identifies the presence of a salicylic acid type photoproduct: The increase in fluorescence intensity and shift to 410 nm (with corresponding excitation maximum near 300 nm) are unmistakable. Evidence for phenyl salicylate and biphenolic type products can also be inferred from the excitation spectra for the photolyzed polycarbonate film in THF shown in Figure 13 for emission wavelengths of 470 nm (phenyl salicylate type product), 410 nm (salicylic acid type product) and 360 nm (biphenolic type product).

In order to formulate a viable mechanism for phenyl salicylate photolysis to give

salicylic acid, one must presume that oxygen is necessary for the formation of the salicylic acid type product. To verify the effect of oxygen on the formation of the salicylic acid, photolysis of a thin polycarbonate film (cast in nitrogen in a dry box to avoid any residual oxygen in the film) was carried out in vacuum. Figure 14 shows the emission spectra of the nitrogen cast polycarbonate film before and after photolysis in vacuum: An increase in fluorescence is observed with peak maxima at 360 nm and 470 nm. The fluorescence from 450-500 nm is due to either a phenyl salicylate type photoproduct, a salicylic acid type photoproduct or both as was found for photolysis in air. In order to determine if salicylic acid is present or not, the spectrum of the film (cast in nitrogen, photolyzed in vacuum, and finally dissolved in THF) was recorded in THF (Figure 15a,b): It is obvious that salicylic acid, which fluoresces around 410 nm in THF, is not present. In addition to the peak at 360 nm, we observe only a weak, broad fluorescence with a maximum around 460 nm (this is quite clear from the expanded view in Figure 15b) which corresponds to the phenyl salicylate type photoproduct (confirmed by a peak around 310 nm in the excitation spectrum, not shown). We conclude that the presence of phenyl salicylate and the lack of salicylic acid (absence of 410 nm emission) in the photolyzed polycarbonate film indicates that oxygen is necessary for the formation of the salicylic acid. This final result is important since during natural weathering, oxygen is present and salicylic acid would be expected to form.

**C. Photolysis of Salicylic Acid and 2,2'-Biphenol**

While our results to this point indicate the formation of salicylic acid and 2,2'-biphenolic type products in the very early stages of photolysis of polycarbonate films, as

well as appropriate model compounds for the carbonate repeat unit in the backbone, we must still indicate the potential importance of these chromophores to degradation phenomena and color formation in polycarbonate. Figures 16 and 17 show the UV spectra of photolyzed DCM solutions of salicylic acid, and 2,2'-biphenol as a function of time. A 450W xenon lamp/monochromator system with a 10 nm spectral band output centered around 310 nm was employed to photolyze the DCM solutions. Although the initial absorbencies at 310 nm were equalized, it should be noted that the spectral overlap of the excitation source (if monochromator bandwidth is taken into account) was greater for salicylic acid than 2,2'-biphenol. In this very rough preliminary analysis of the photolability (with respect to color formation) of the two photoproducts identified herein to form in the early stages of polycarbonate (or diaryl carbonate) photolysis, it seems obvious that both 2,2'-biphenol and salicylic acid are active in color production with 2,2'-biphenol being the more photolabile. Hence, the early detection of salicylic acid and 2,2'-biphenol in the photolysis of polycarbonate films is important in assessment of the overall discoloration process.

Finally, it should be mentioned that we have found that photolysis of polycarbonate film in sunlight leads to formation of fluorescent photoproducts upon exposure time of only a few days. Thus the present study is important in providing a sound framework for critical analysis of polycarbonate photolysis in sunlight via fluorescence spectroscopy. In a separate publication, we will expand upon this subject.

## Conclusions

In this paper, fluorescence analysis of polycarbonate and its model compounds in DCM and THF has allowed the study of various aspects of the photolytic decomposition of polycarbonate. Our results are in concert with published literature reports as exemplified in references 16 and 20, and underscore the importance of early detection and identification of primary photoproducts, which themselves are often photolabile (as pointed out in this paper and the results in references 14 and 16). Results from our study indicate that:

1. Fluorescence spectroscopy is a sensitive and a selective technique that can be used to differentiate between phenyl salicylate and salicylic acid type products formed in the very early stages of photolysis of polycarbonate and its model compounds.
2. Fluorescence analysis was utilized to detect 2,2'-biphenol type products in polycarbonate and its model compounds in the initial stages of photolysis.
3. Oxygen is needed for the formation of salicylic acid type products in photolyzed polycarbonate films.
4. Salicylic acid and 2,2'-biphenol are photolabile and form colored products on photolysis, thus contributing towards discoloration of polycarbonate.

The utility of fluorescence as an effective technique for early detection of several photoproducts at the initial stages of the photolysis process is clearly evident. Detection

of key products during the early stages of photolysis of polycarbonate in sunlight and at wavelengths greater than 300 nm will be addressed in the next paper in this series.

**Acknowledgements**

The authors acknowledge the financial support of the Office of Naval Research and Ciba-Geigy Corporation (Ciba Additives). We also thank Peter Klemchuk (Ciba-Geigy) and David Creed (Chemistry, USM) for invaluable discussions.

## References and Notes


(1) E. S. Sherman, A. Ram, and S. Kenig, *Polym. Eng. Sci.*, **1982**, *22(8)*, 457.

(2) A. Ram, O. Zilber, and S. Kenig, *Polym. Eng. Sci.*, **1985**, *25(9)*, 535.

(3) D. Bellus, P. Hrdlovic, and Z. Manasek, *J. Polym. Sci. Part B: Polym. Lett.*, **1966**, *4*, 1.

(4) B. D. Gesner and P. G. Kelleher, *J. Appl. Polym. Sci.*, **1969**, *13*, 2183.

(5) P. A. Mullen and N. Z. Searle, *J. Appl. Polym. Sci.*, **1970**, *14*, 765.

(6) J. S. Humphrey, Jr., and R. S. Roller, *Mol. Photochem.*, **1971**, *3(1)*, 35.

(7) J. S. Humphrey, Jr., A. R. Shultz, and D. B. G. Jaquiss, *Macromolecules*, **1973**, *6*, 305.

(8) A. Gupta, A. Rembaum, and J. Moacanin, *Macromolecules*, **1978**, *11*, 1285.

(9) K. B. Abbas, *J. Appl. Polym. Sci. Appl. Polym. Symp.*, **1979**, *35*, 345.

(10) A. Gupta, R. Liang, J. Moacanin, R. Goldbeck, and D. Kliger, *Macromolecules*, **1980**, *13*, 262.

(11) A. Factor and M. L. Chu, *Polym. Degrad. Stab.*, **1980**, *2*, 203.

(12) J. E. Moore, *ACS Symp. Ser.*, **1981**, *151*, 97.

(13) D. T. Clark and H. S. Munro, *Polym. Degrad. Stab.*, **1982**, *4*, 441.

(14) A. Rivaton, D. Sallet, and J. Lemaire, *Polym. Photochem.*, **1983**, *3*, 463.

(15) C. A. Pryde, *ACS Symp. Ser.*, **1985**, *280*, 329.

(16) A. Rivaton, D. Sallet, and J. Lemaire, *Polym. Degrad. Stab.*, **1986**, *14*, 1.

(17) A. Rivaton, D. Sallet, and J. Lemaire, *Polym. Degrad. Stab.*, **1986**, *14*, 23.

(18) J. Lemaire, J. L. Gardette, A. Rivaton, and A. Roger, *Polym. Degrad. Stab.*, **1986**,

*15*, 1.

(19) J. D. Webb and A. W. Czanderna, *Macromolecules*, **1986**, *19*, 2810.

(20) A. Factor, W. V. Ligon, and R. J. May, *Macromolecules*, **1987**, *20*, 2461.

(21) A. Factor, J. C. Lynch, and F. H. Greenberg, *J. Polym. Sci. Part A: Polym. Chem.*, **1987**, *25*, 3413.

(22) M. C. Gupta and G. V. Tahilyani, *Colloid Polym. Sci.*, **1988**, *266*, 620.

(23) M. C. Gupta and R. R. Pandey, *Makromol. Chem. Macromol. Symp.*, **1989**, *27*, 245.

(24) A. Davis and J. H. Golden, *J. Chem. Soc. (B)*, **1968**, 425.

(25) W. M. Horspool and P. L. Pauson, *J. Chem. Soc.*, **1965**, 5162.

(26) C. E. Hoyle, H. Shah, and G. L. Nelson, *J. Polym. Sci. Part A: Polym. Chem.*, **1992**, *30*, 1525.

(27) J. Yongcai, W. Zhuaeng, and W. Shikang, *Ganguang Kexue Yu Kuang Huaxue*, **1986**, *3*, 42.

(28) C. D. Pande and B. Venkataramani, *Indian J. Technol.*, **1966**, *4(11)*, 342.

## Figure Captions

Figure 1a Normalized fluorescence emission spectra ($\lambda_{ex}$ = 310 nm) of phenyl salicylate (5 x $10^{-5}$ M) and salicylic acid (5 x $10^{-5}$ M) in DCM.

Figure 1b Normalized fluorescence excitation spectra of phenyl salicylate (5 x $10^{-5}$ M, $\lambda_{em}$ = 470 nm) and salicylic acid (5 x $10^{-5}$ M, $\lambda_{em}$ = 460 nm) in DCM.

Figure 2a Fluorescence emission spectra ($\lambda_{ex}$ = 310 nm) of DPC (4.5 x $10^{-3}$ M) in DCM for 0, 1, and 3 min. photolysis in Rayonet Reactor with 300 nm lamps (reproduced from reference 26).

Figure 2b Fluorescence emission spectra ($\lambda_{ex}$ = 310 nm) of DPC (4.5 x $10^{-3}$ M) in THF for 0, 3, and 7 min. photolysis in Rayonet Reactor with 300 nm lamps.

Figure 3a Normalized fluorescence emission spectra ($\lambda_{ex}$ = 310 nm) of phenyl salicylate (5 x $10^{-5}$ M) and salicylic acid (5 x $10^{-5}$ M) in THF.

Figure 3b Normalized fluorescence excitation spectra of phenyl salicylate (5 x $10^{-5}$ M, $\lambda_{em}$ = 470 nm) and salicylic acid (5 x $10^{-5}$ M, $\lambda_{em}$ = 410 nm) in THF.

Figure 4 Normalized fluorescence excitation spectra ($\lambda_{em}$ = 400 and 470 nm) of DPC (4.5 x $10^{-3}$ M) in THF photolyzed for 3 min. in Rayonet Reactor with 300 nm lamps. Scatter peak around 355 nm has been removed artificially.

Figure 5 Fluorescence emission spectra ($\lambda_{ex}$ = 310 nm) of phenyl salicylate (5 x $10^{-5}$ M) in DCM for 0, 1, and 6 min. photolysis in Rayonet Reactor with 300 nm lamps.

Figure 6 Fluorescence emission spectra ($\lambda_{ex}$ = 310 nm) of phenyl salicylate (4.9 x $10^{-5}$ M) in THF for 0, 2, 5, and 10 min. photolysis in Rayonet Reactor

with 300 nm lamps.

Figure 7a Fluorescence emission spectra ($\lambda_{ex}$ = 310 nm) of bis(phenyl carbonate) of bisphenol-A (5.5 x $10^{-4}$ M) in THF for 0, 3, 7, and 15 min. photolysis in Rayonet Reactor with 300 nm lamps.

Figure 7b Fluorescence excitation spectra ($\lambda_{em}$ = 400 and 470 nm) of bis(phenyl carbonate) of bisphenol-A (5.5 x $10^{-4}$ M) in THF photolyzed for 3 min in Rayonet Reactor with 300 nm lamps. Scatter peak around 355 nm has been removed artificially.

Figure 8 Fluorescence emission spectrum ($\lambda_{ex}$ = 310 nm) of 2,2'-biphenol (5 x $10^{-5}$ M) in THF.

Figure 9a Fluorescence emission spectra ($\lambda_{ex}$ = 310 nm) of polycarbonate (6.4 x $10^{-4}$ M) in THF for 0, 3, and 7 min. photolysis in Rayonet Reactor with 300 nm lamps.

Figure 9b Fluorescence excitation spectra ($\lambda_{em}$ = 400 nm) of polycarbonate (6.4 x $10^{-4}$ M) in THF for 0, 3, and 7 min. photolysis in Rayonet Reactor with 300 nm lamps.

Figure 10 Normalized fluorescence excitation spectra ($\lambda_{em}$ = 370, 400, and 470 nm) of polycarbonate (6.4 x $10^{-4}$ M) in THF photolyzed for 3 min. in Rayonet Reactor with 300 nm lamps. Scatter peaks around 335 nm and 355 nm have been removed artificially.

Figure 11 Fluorescence emission spectra ($\lambda_{ex}$ = 325 nm) of polycarbonate film before and after photolysis for 15 min. in Rayonet Reactor with 300 nm lamps.

Figure 12a Fluorescence emission spectrum ($\lambda_{ex}$ = 310 nm) of photolyzed polycarbonate film in DCM ($6.5 \times 10^{-4}$ M). Polycarbonate film was photolyzed for 15 min. in Rayonet Reactor with 300 nm lamps.

Figure 12b Fluorescence emission spectrum ($\lambda_{ex}$ = 310 nm) of photolyzed polycarbonate film in THF ($6.5 \times 10^{-4}$ M). Polycarbonate film was photolyzed for 15 min. in Rayonet Reactor with 300 nm lamps.

Figure 13 Fluorescence excitation spectra ($\lambda_{em}$ = 360, 410, and 470 nm) of photolyzed polycarbonate film in THF ($6.5 \times 10^{-3}$ M). Polycarbonate film was photolyzed for one hour in flowing oxygen in Rayonet Reactor with 300 nm lamps. Scatter peak around 365 nm has been removed artificially.

Figure 14 Fluorescence emission spectra ($\lambda_{ex}$ = 325 nm) of nitrogen cast polycarbonate film before and after one hour photolysis in vacuum in Rayonet Reactor with 300 nm lamps.

Figure 15a Fluorescence emission spectrum ($\lambda_{ex}$ = 310 nm) of photolyzed nitrogen cast polycarbonate film in THF ($6.5 \times 10^{-3}$ M). Polycarbonate (nitrogen cast) film was photolyzed for one hour in vacuum in Rayonet Reactor with 300 nm lamps.

Figure 15b Expanded view of Figure 15a.

Figure 16 UV-Visible spectra of salicylic acid (OD = 0.2 at 310 nm) in DCM for 0, 5, and 10 hour photolysis at 310 nm (10 nm bandpass, 450W Xe lamp).

Figure 17 UV-Visible spectra of 2,2'-biphenol (OD = 0.2 at 310 nm) in DCM for 0, 5, and 10 hour photolysis at 310 nm (10 nm bandpass, 450W Xe lamp).

Table I

**Fluorescence emission and UV-visible absorption maxima of possible model photolysis products recorded in DCM.**

| Compound | $\lambda_{Absorption}$, nm (maximum) | $\lambda_{Fluorescence}$, nm (maximum) |
|---|---|---|
| 4-Hydroxy Benzoic Acid Phenyl Ester (in THF) | 261 | 315 - 330 |
| Phenyl Formate | 262 | 302 |
| Phenol | 271 | 300 |
| Diphenyl Ether | 272 | 300 |
| 2-Phenyl Phenol | 284 | 333 |
| 2,2'-Biphenol (in THF) | 282 | 350 |
| 4,4'-Biphenol (in THF) | 265 | 352 |
| t-Butyl Phenol | 276 | 305 |

## Scheme I: Photo-Fries Rearrangement

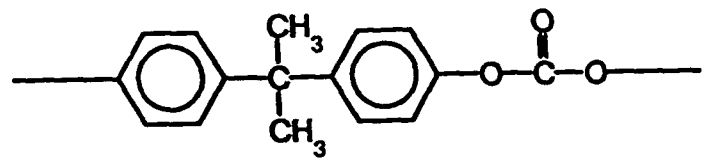




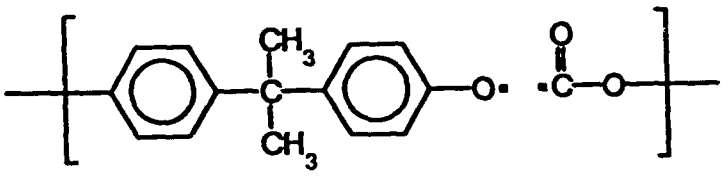

Radical Cage

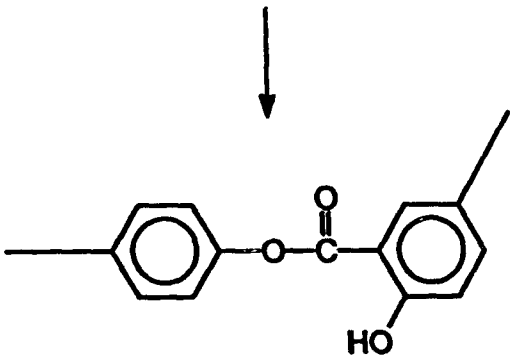

Phenyl Salicylate Type




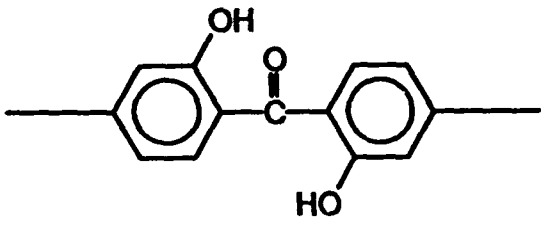

2,2'-Dihydroxybenzophenone Type

## Scheme II: Coupling Products

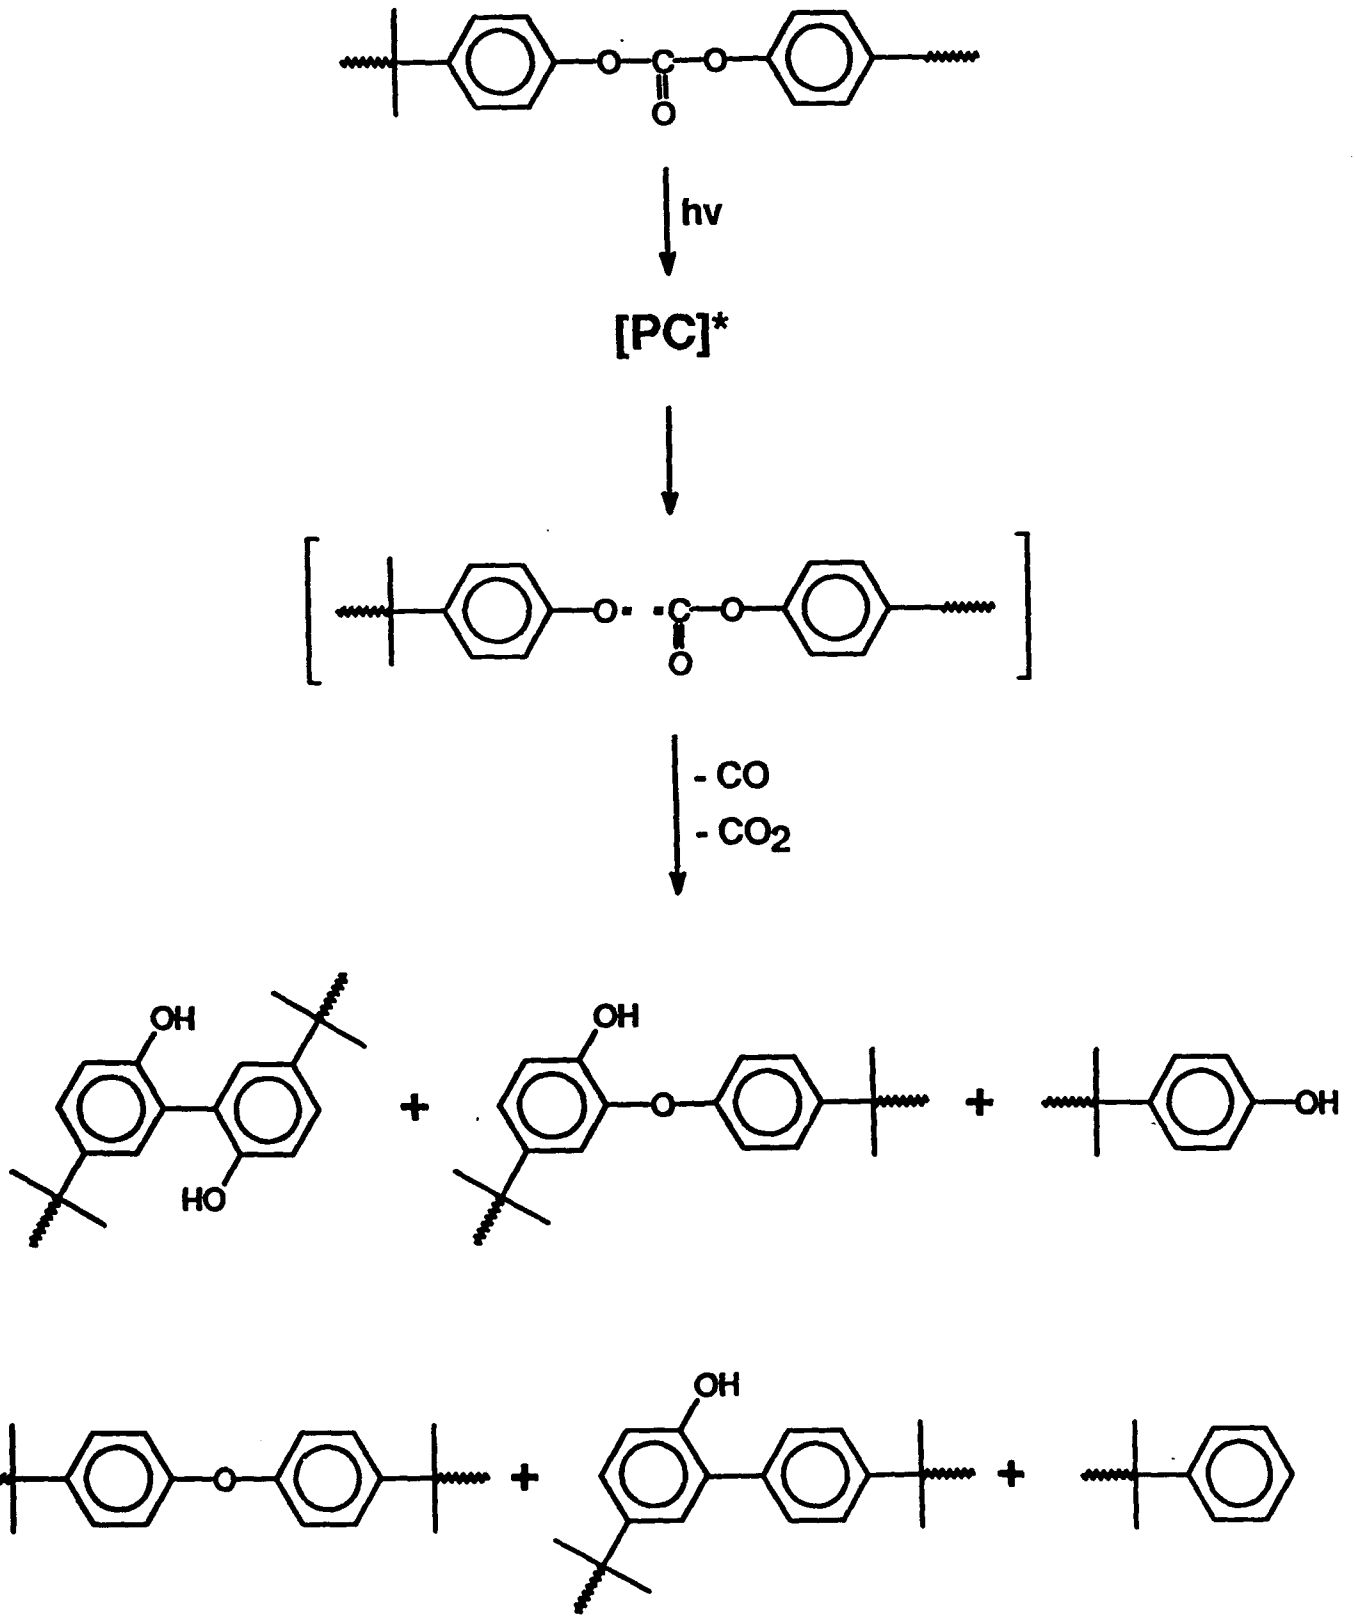

Fig. 1a

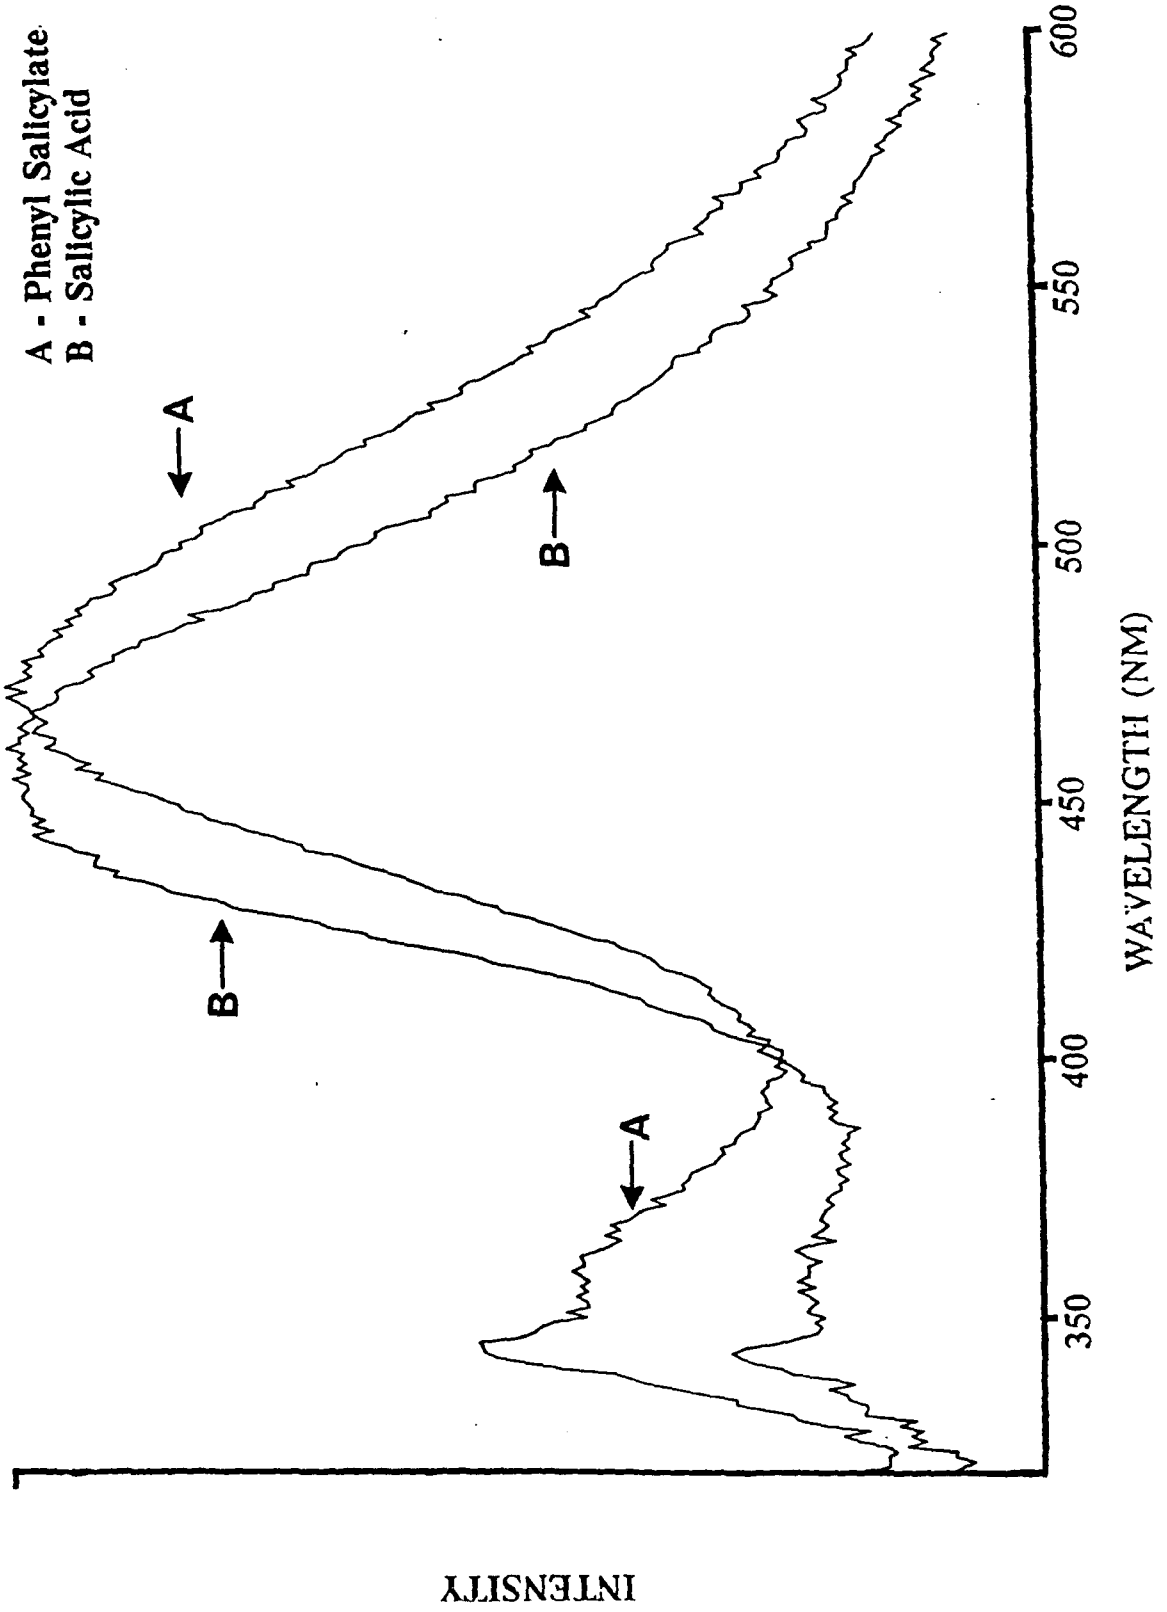
A - Phenyl Salicylate
B - Salicylic Acid
A
B
B
A
350
400
450
500
550
600
WAVELENGTH (NM)
INTENSITY

Fig. 1b

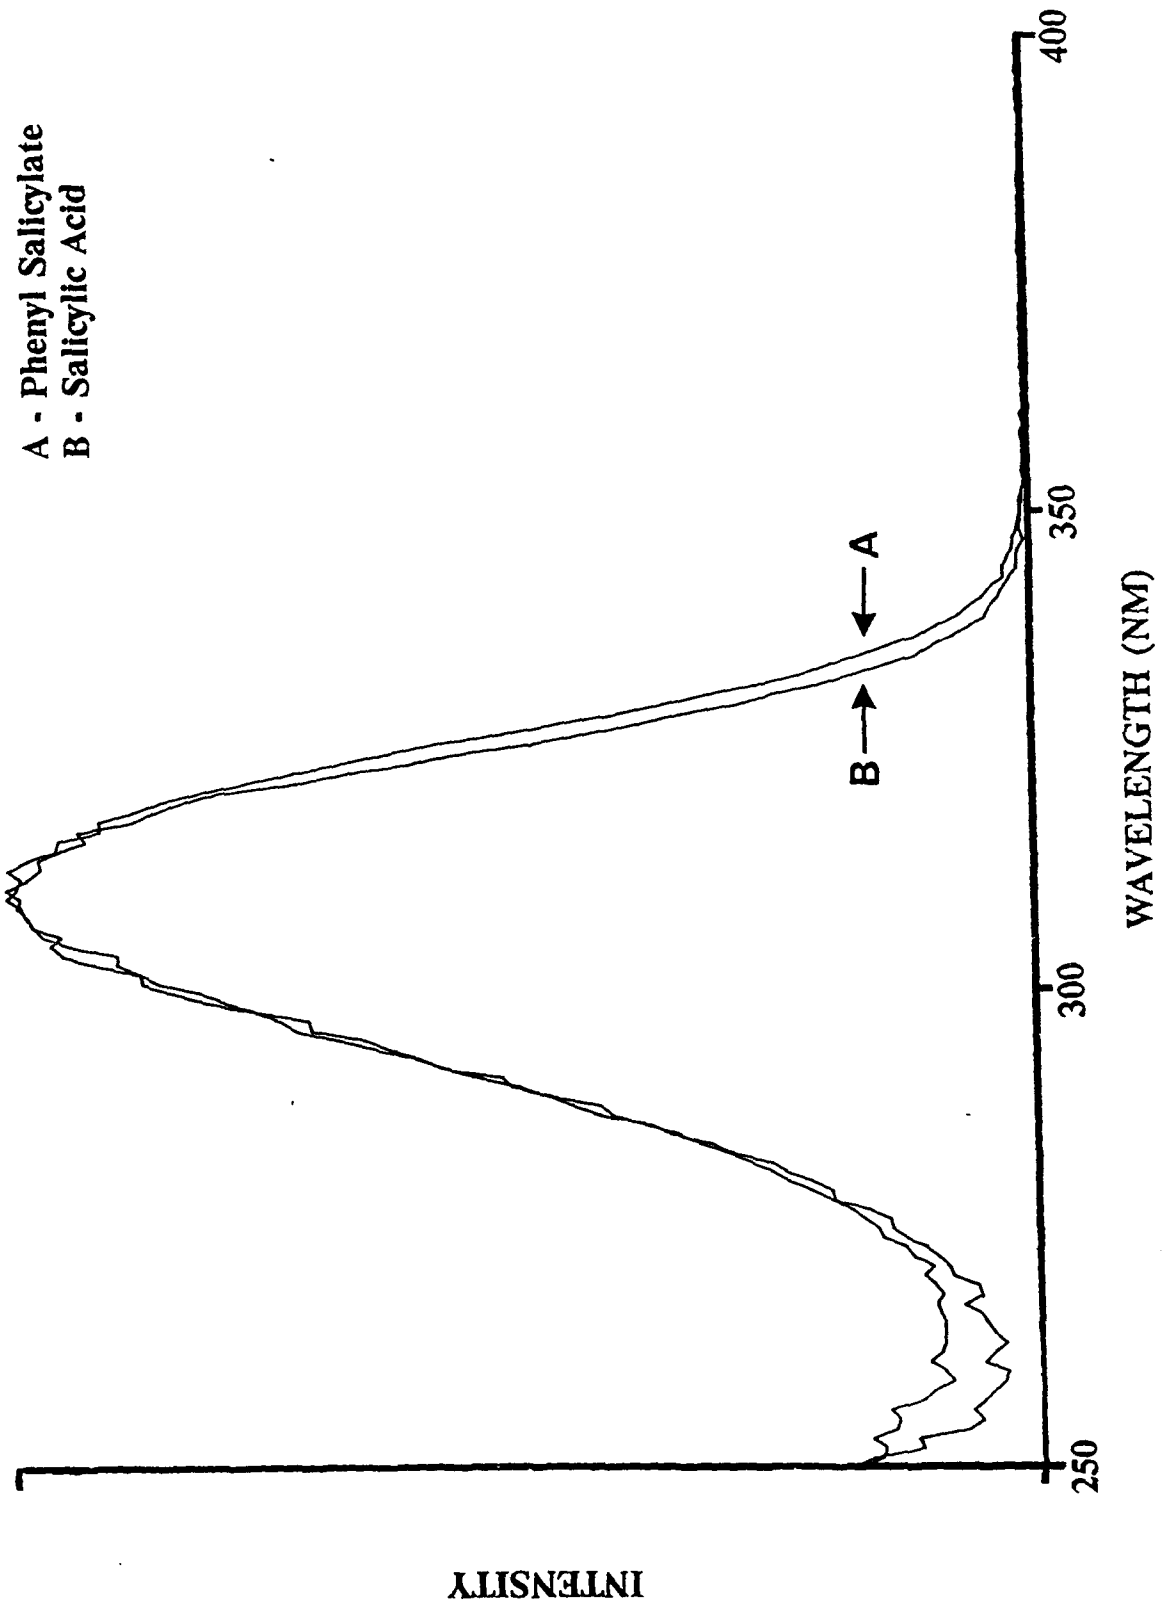
A - Phenyl Salicylate
B - Salicylic Acid
A
B
250
300
350
400
WAVELENGTH (NM)
INTENSITY

Fig. 2G

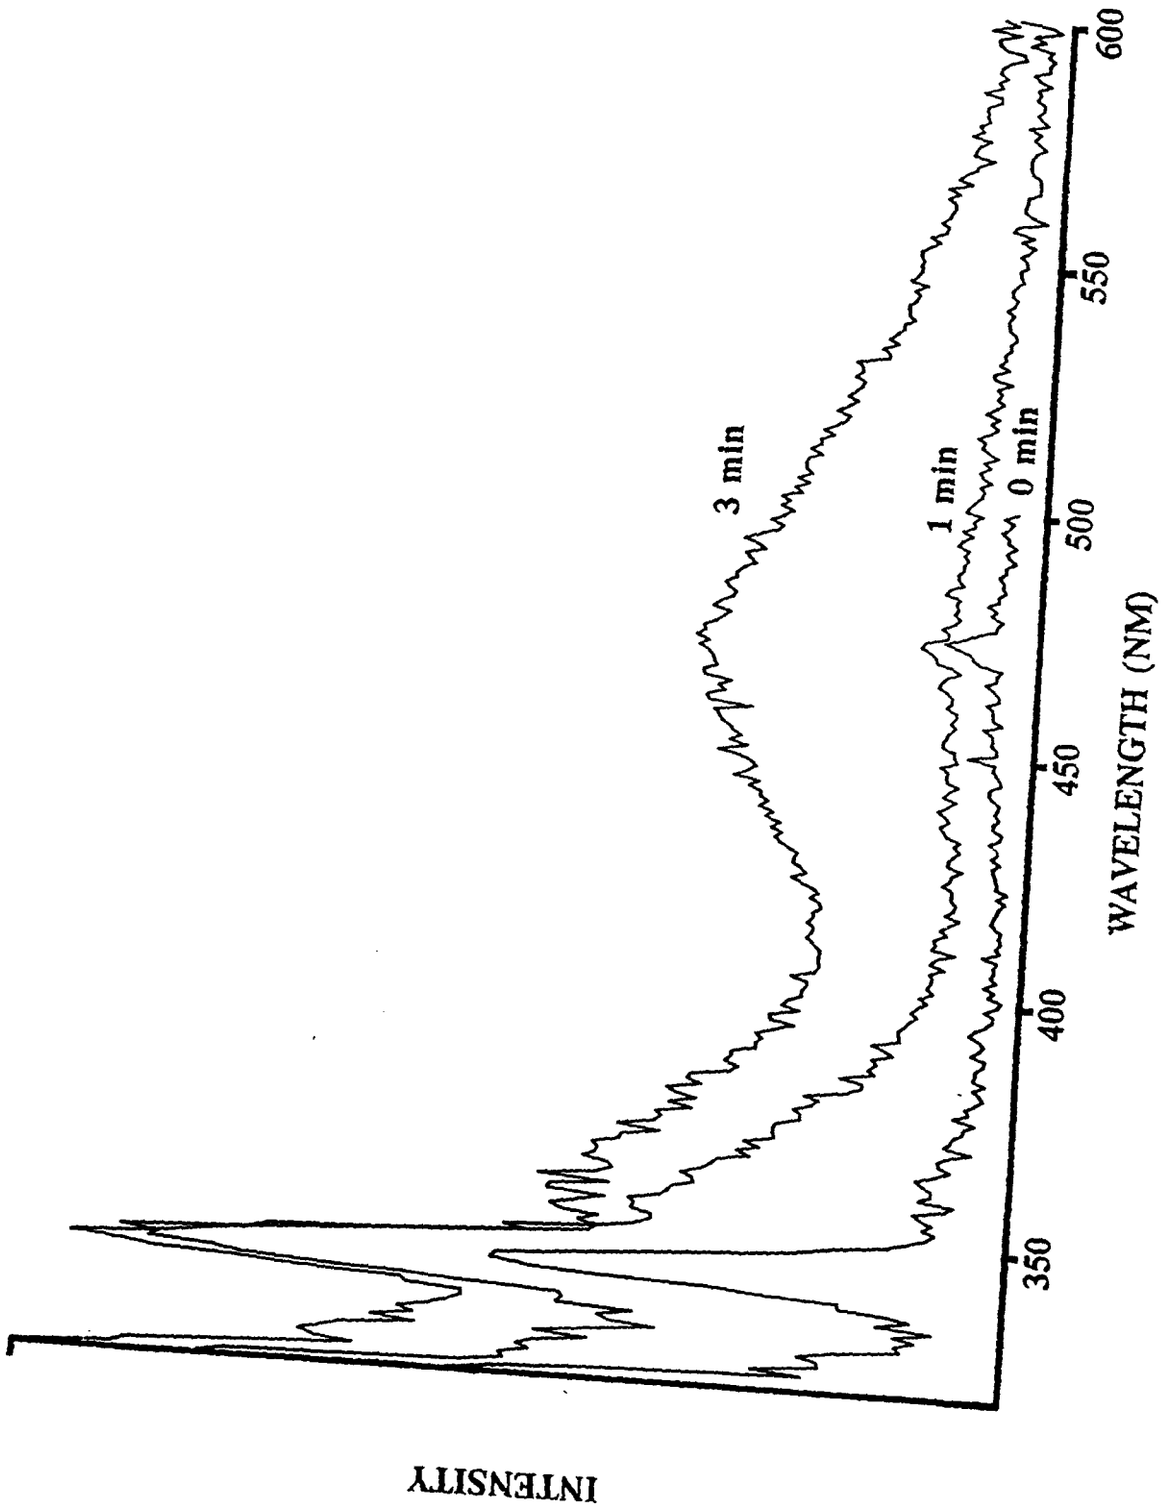
3 min
1 min
0 min
350
400
450
500
550
600
WAVELENGTH (NM)
INTENSITY

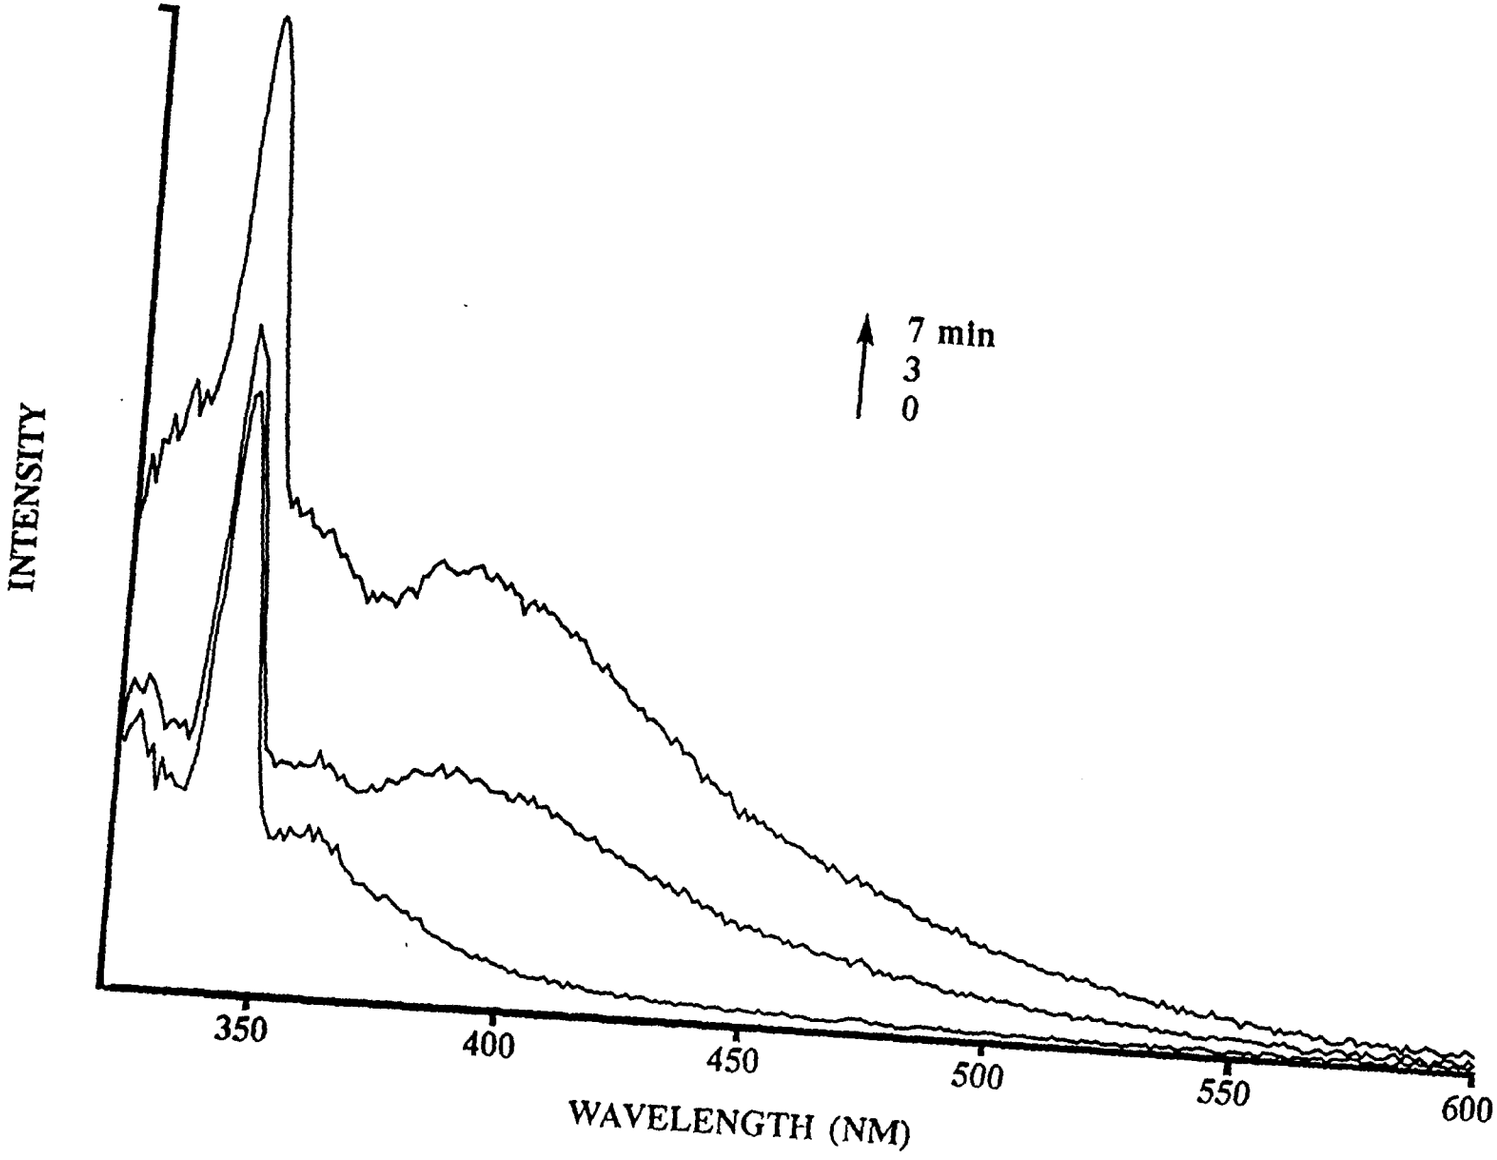


Fig. 2a

Fig. 3a

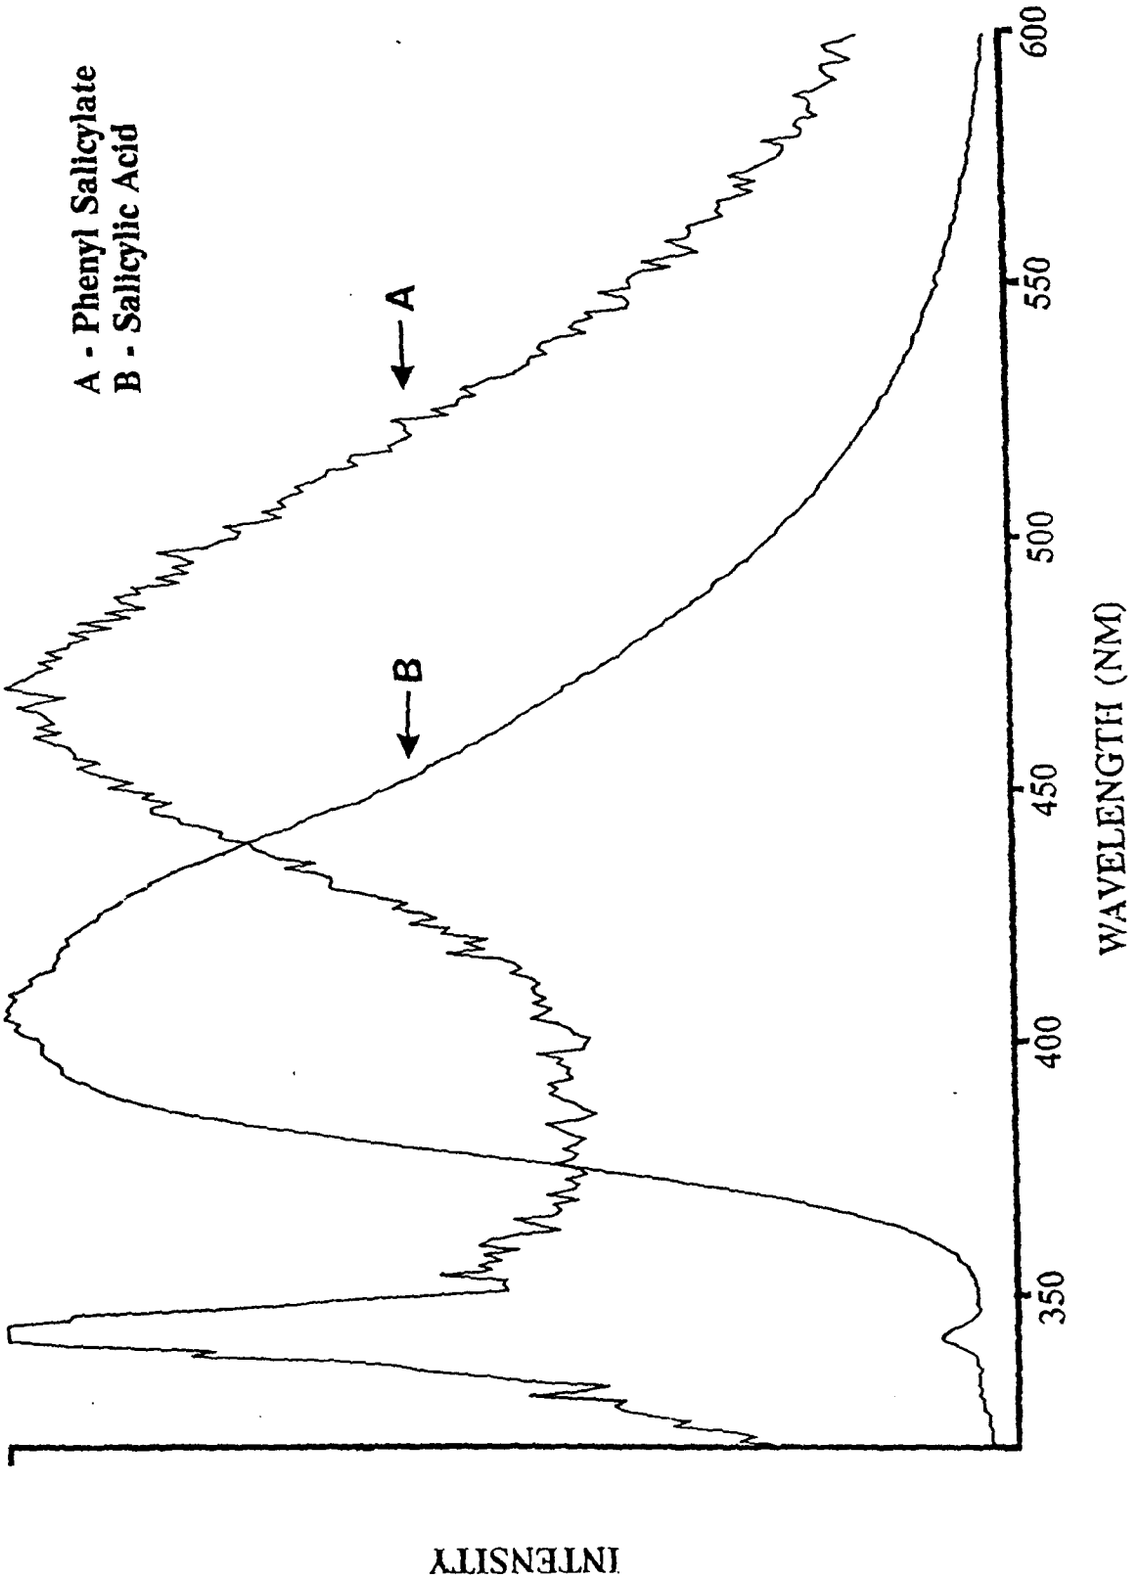
A - Phenyl Salicylate
B - Salicylic Acid
A
B
350
400
450
500
550
600
WAVELENGTH (NM)
INTENSITY

Fig. 3b

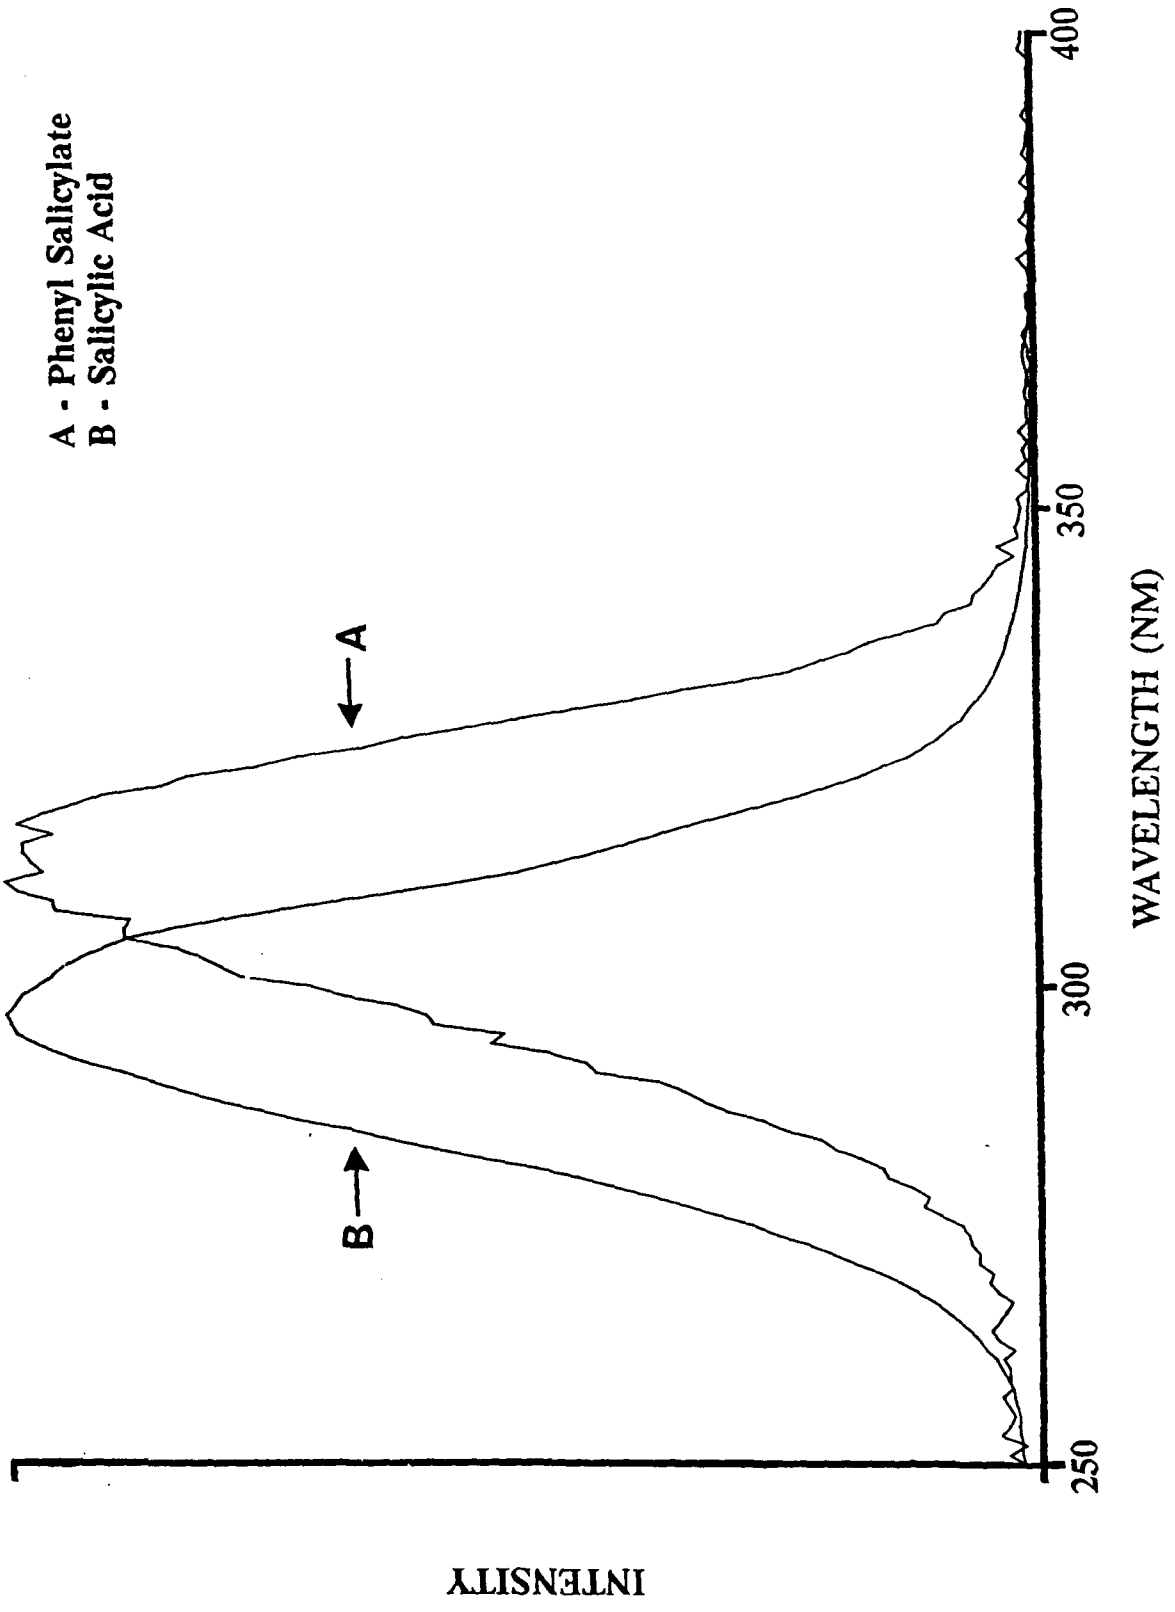
A - Phenyl Salicylate
B - Salicylic Acid
A
B
250
300
350
400
WAVELENGTH (NM)
INTENSITY

Fig. 4

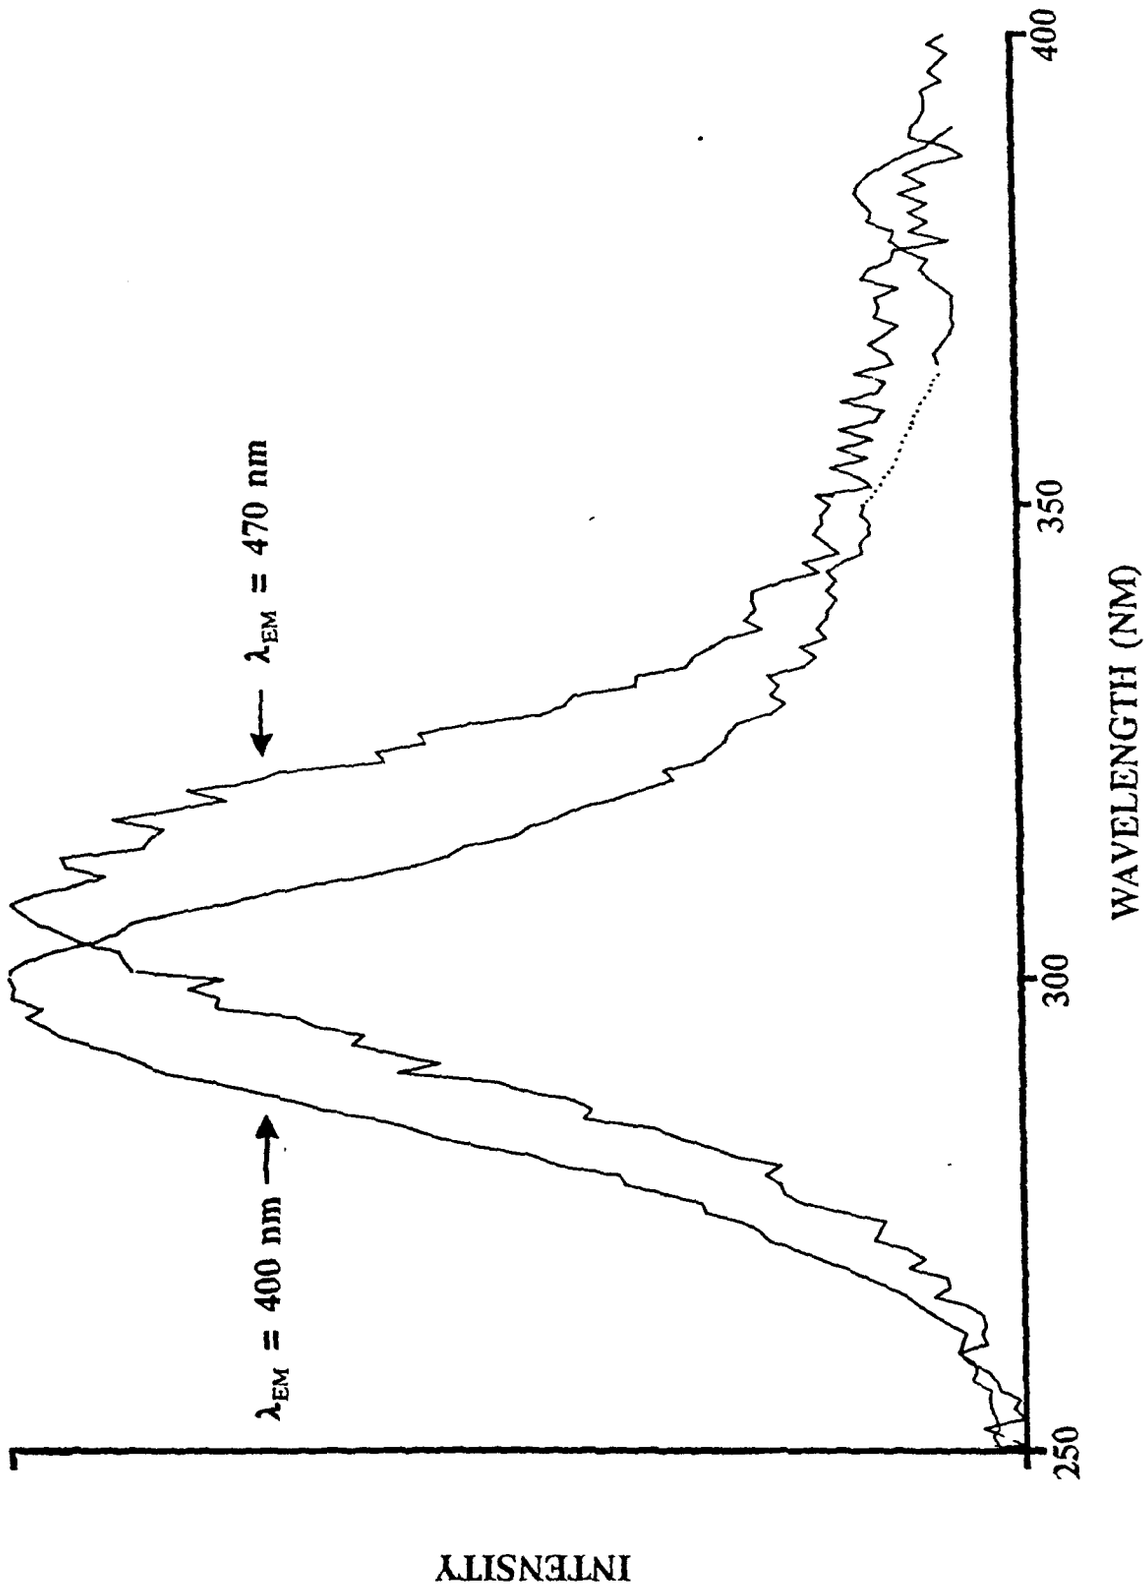
$\lambda_{EM}$ = 470 nm
$\lambda_{EM}$ = 400 nm
250
300
350
400
WAVELENGTH (NM)
INTENSITY

Fig. 5

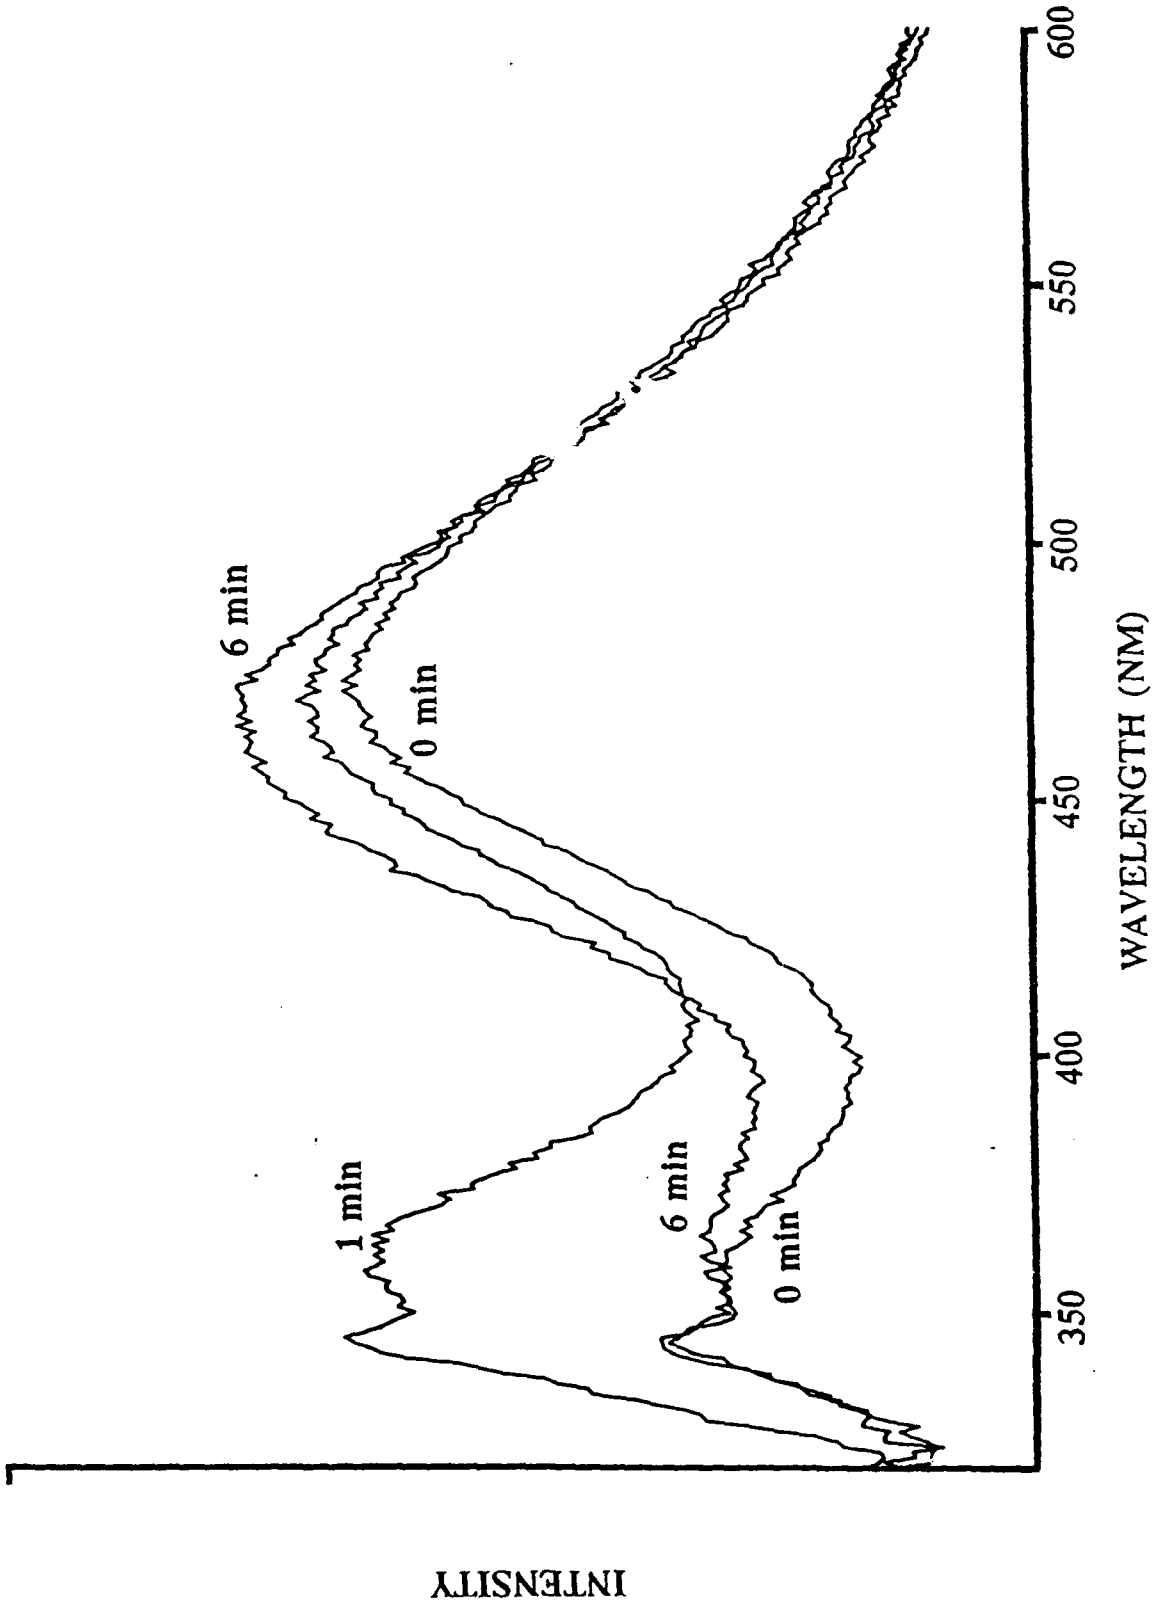
INTENSITY
WAVELENGTH (NM)
350
400
450
500
550
600
1 min
6 min
0 min
6 min
0 min

Fig. 6

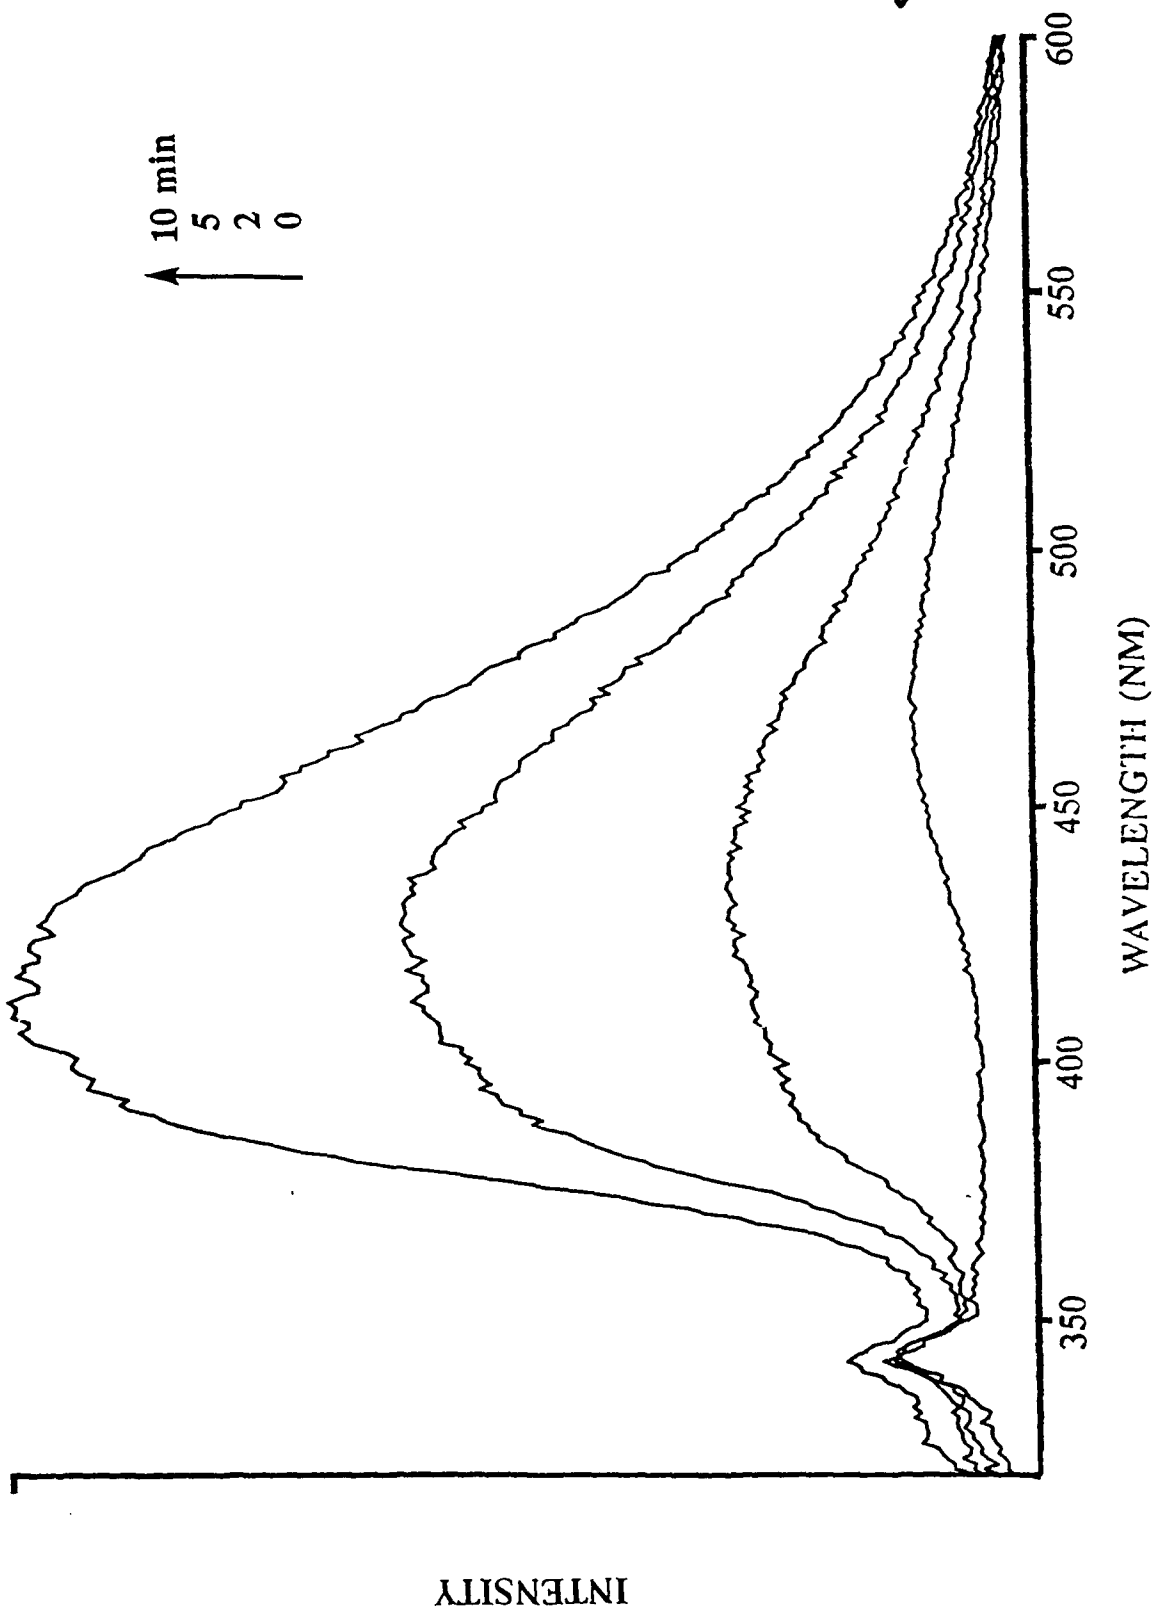

Fig. 7a

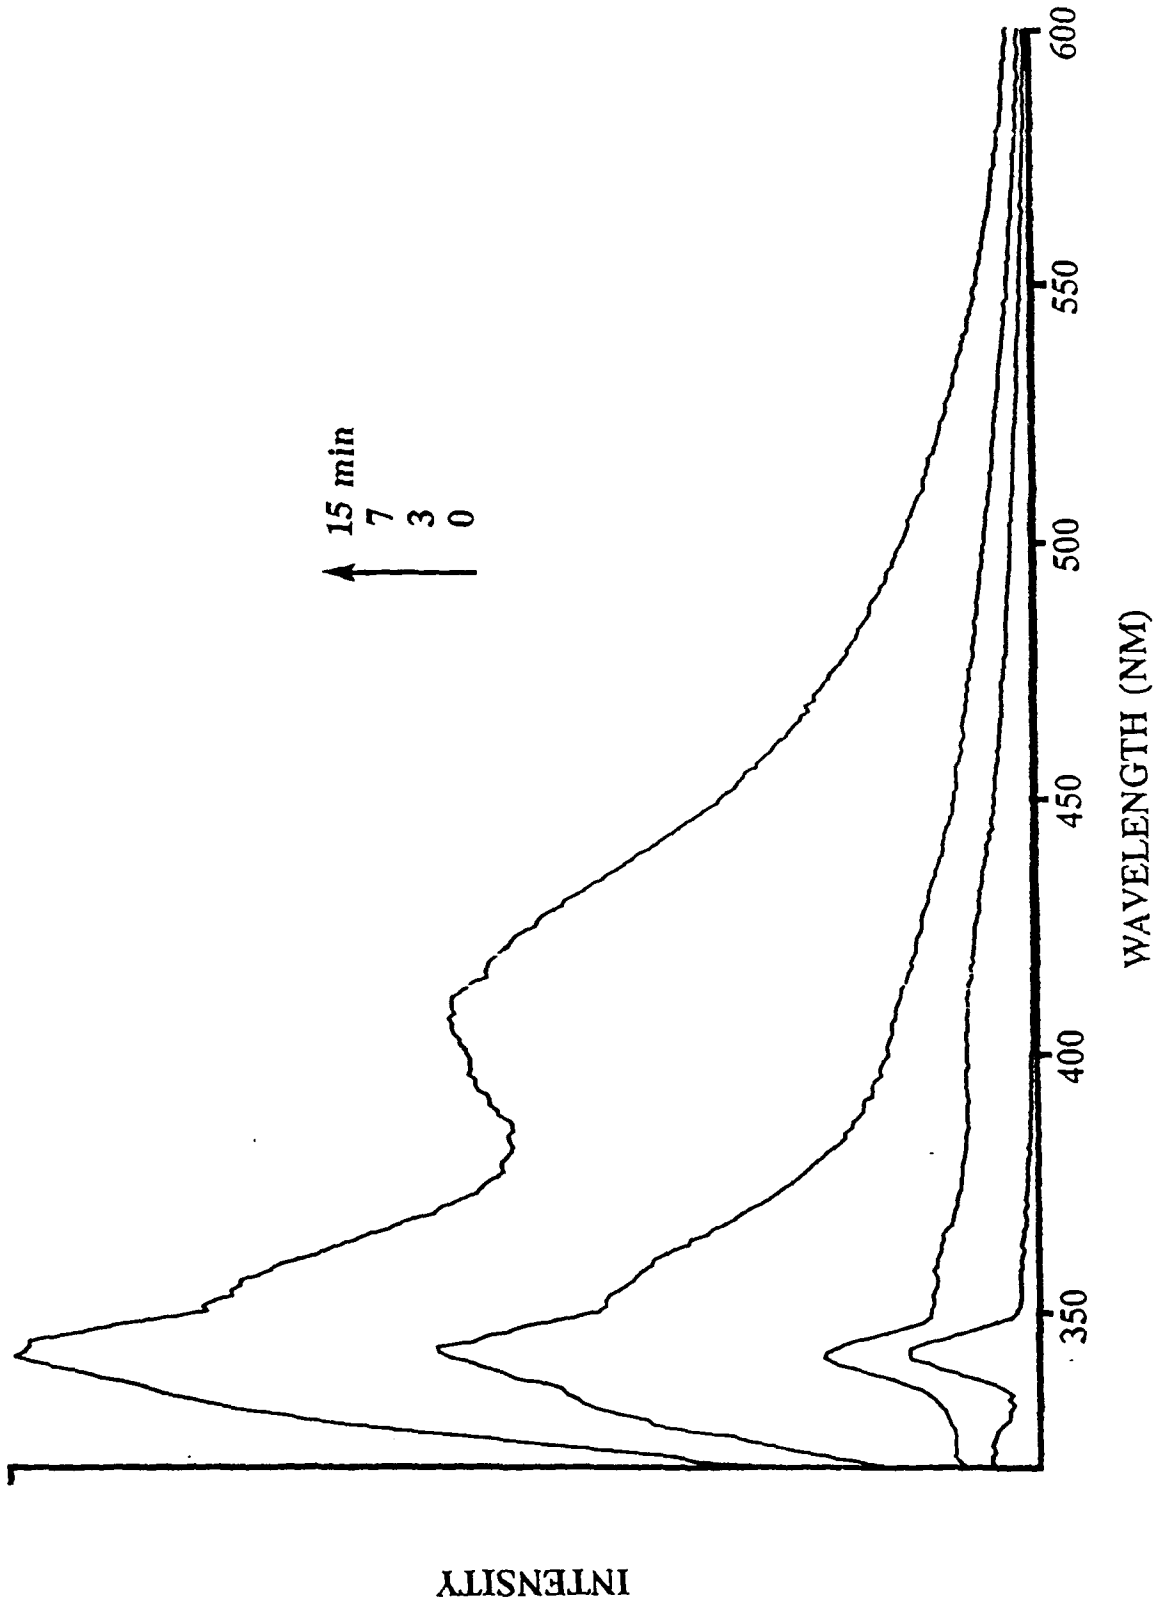

Fig. 7b

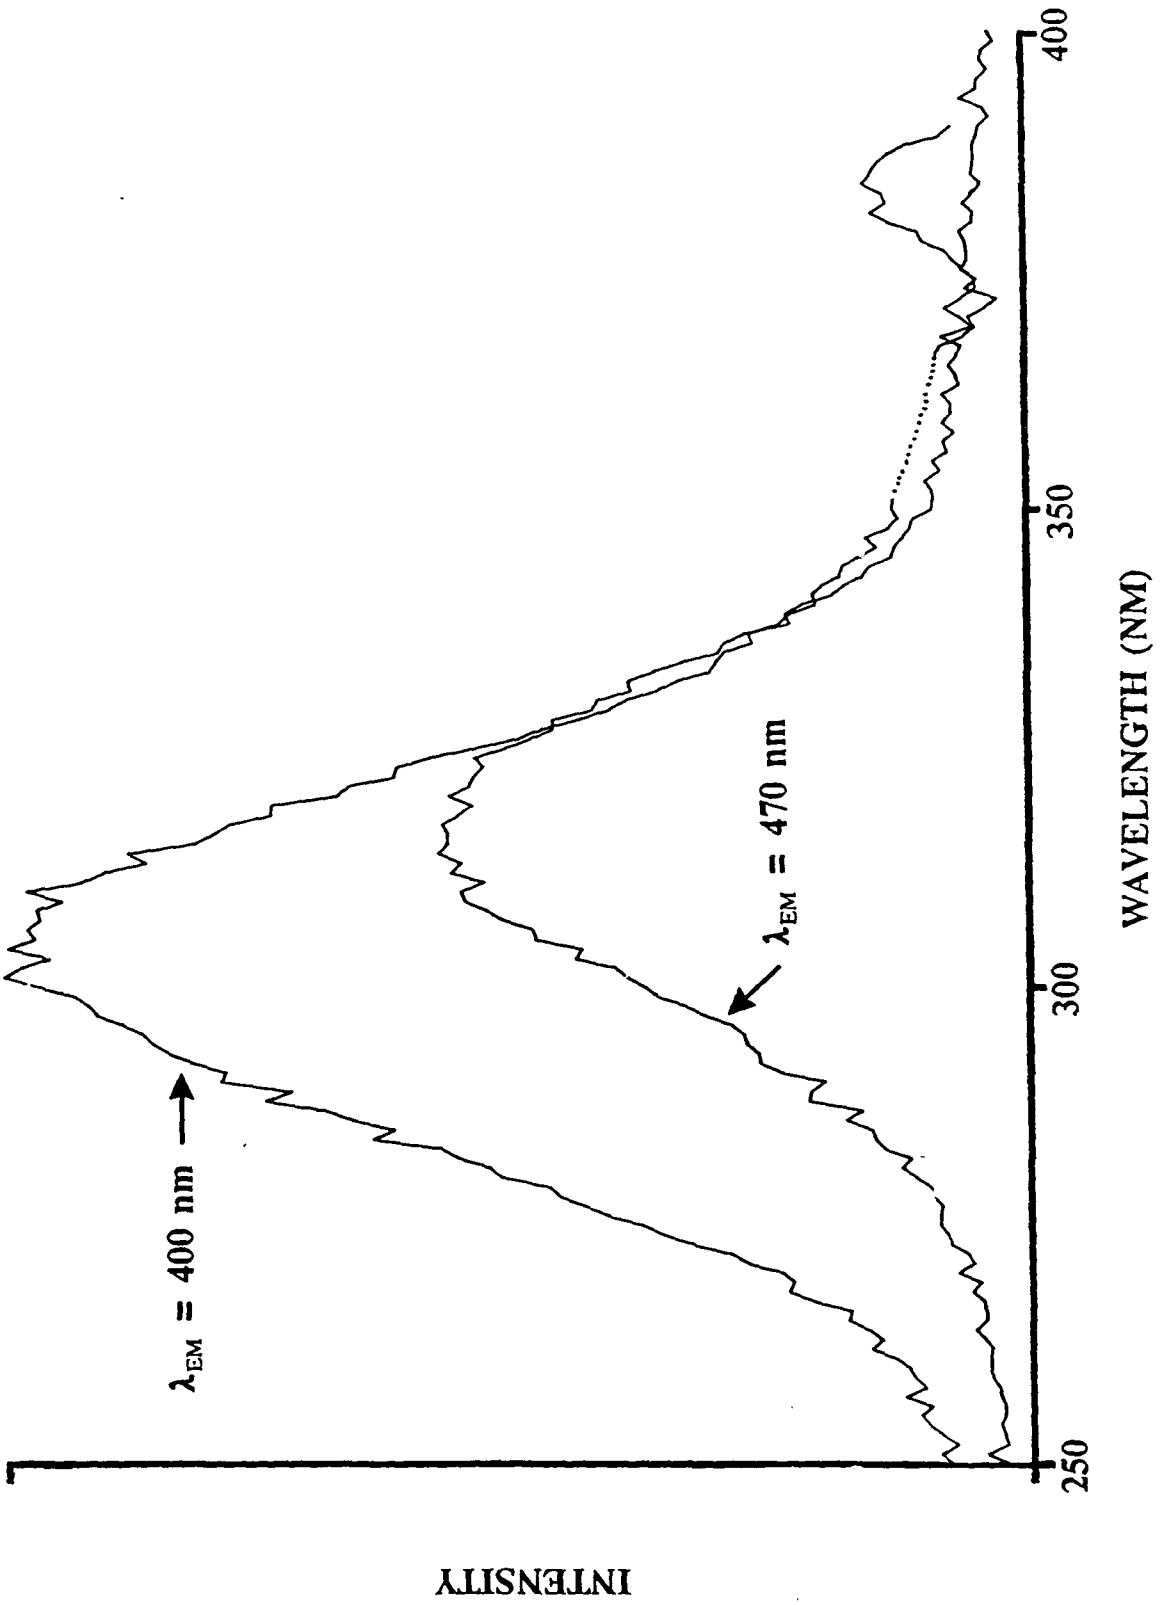
INTENSITY
250
300
350
400
WAVELENGTH (NM)
$\lambda_{EM}$ = 400 nm
$\lambda_{EM}$ = 470 nm

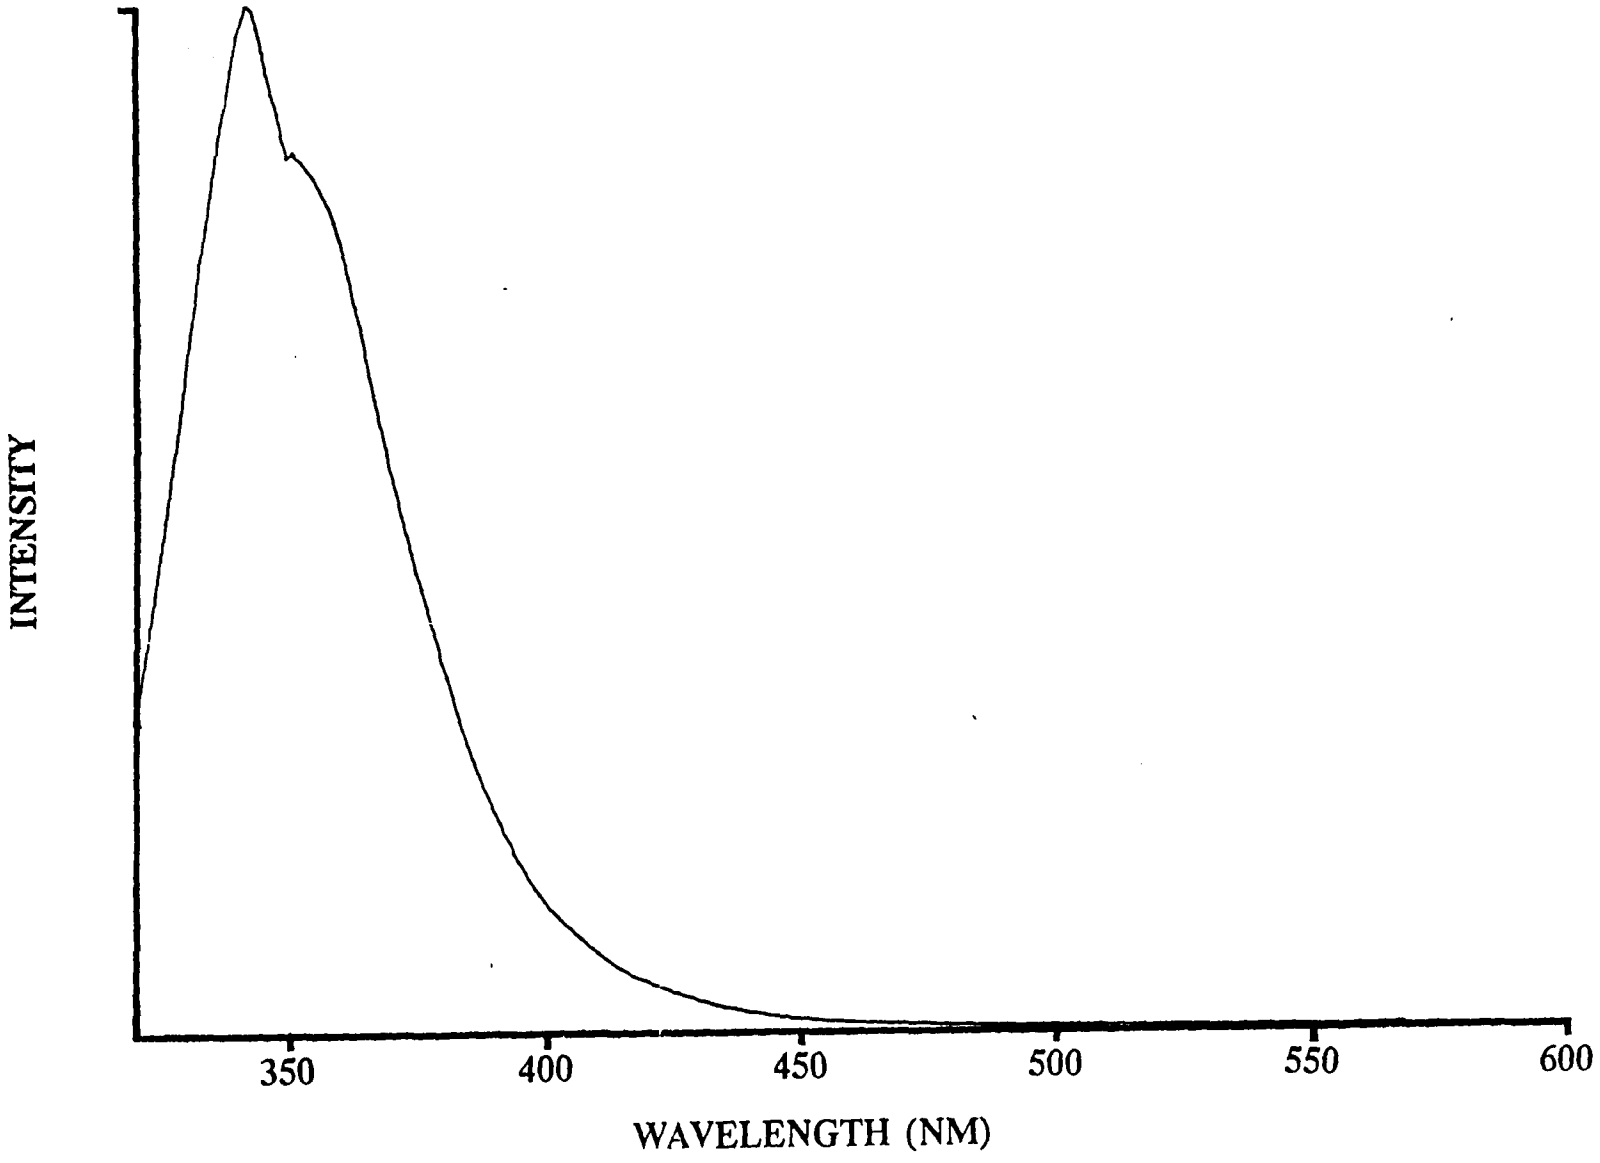


Fig. 8.1

Fig. 9a

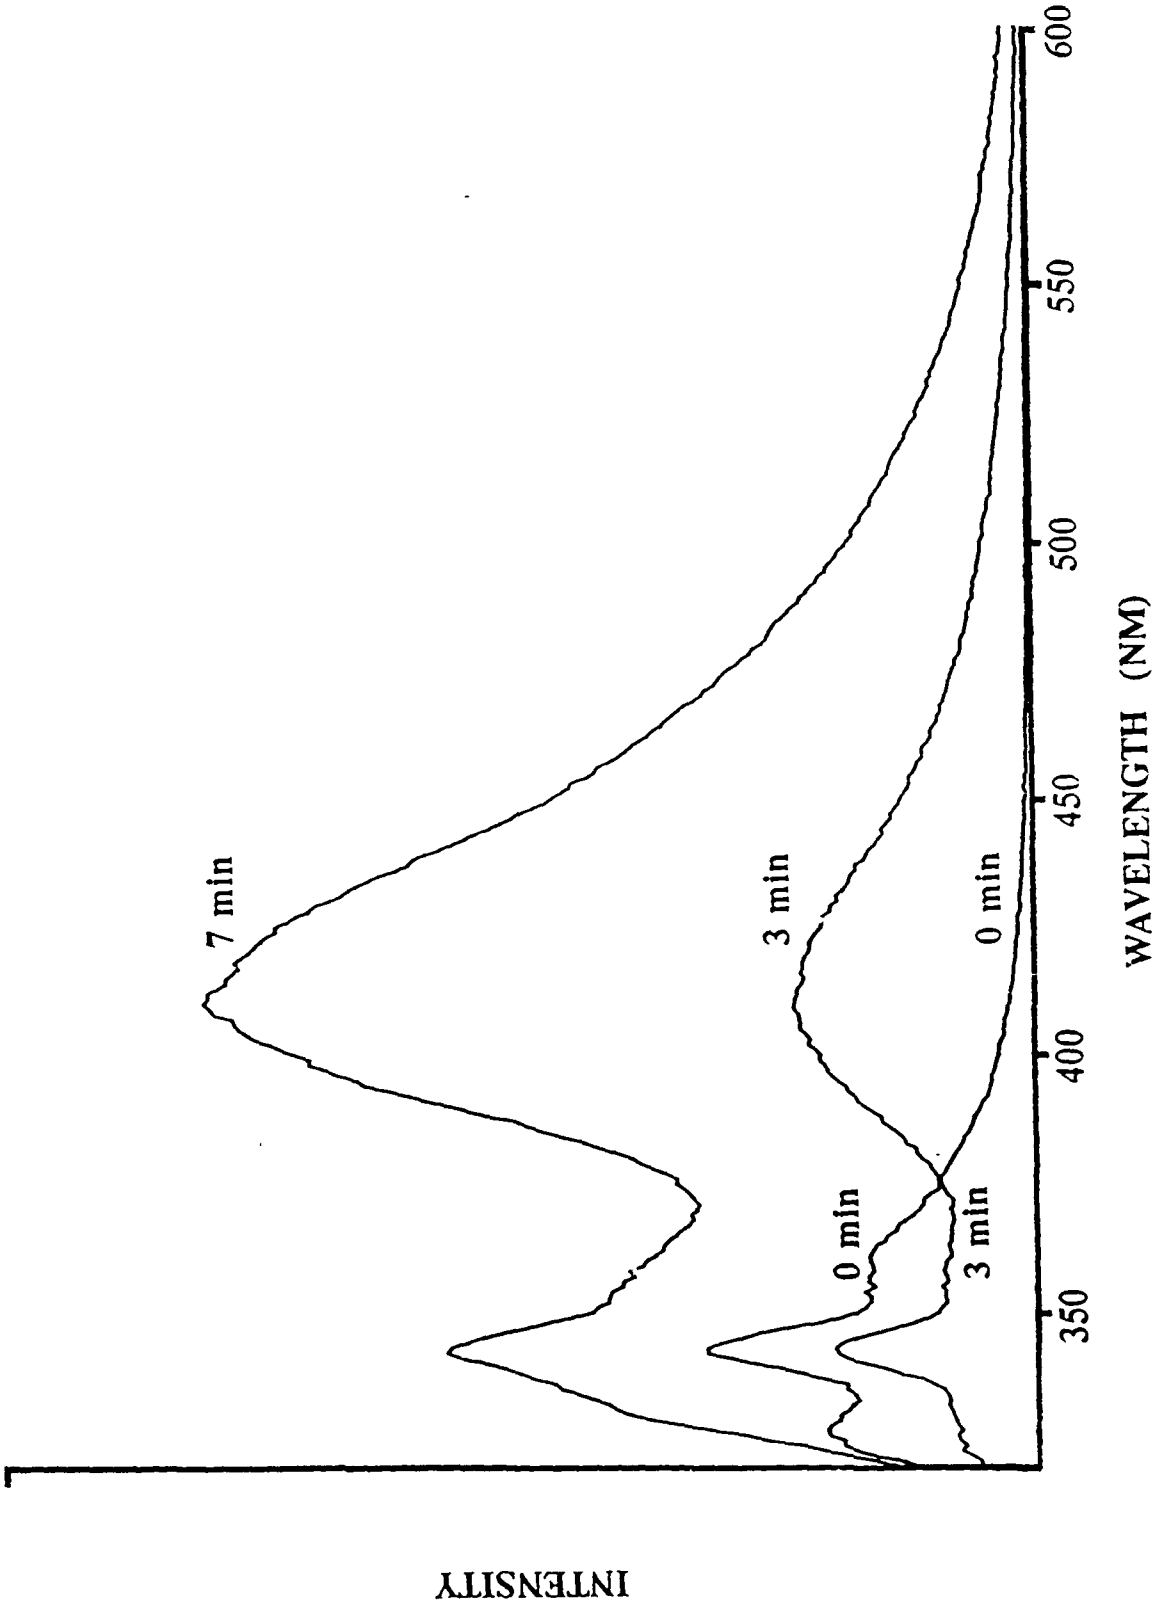
7 min
3 min
0 min
0 min
3 min
350
400
450
500
550
600
WAVELENGTH (NM)
INTENSITY

Fig. 9b

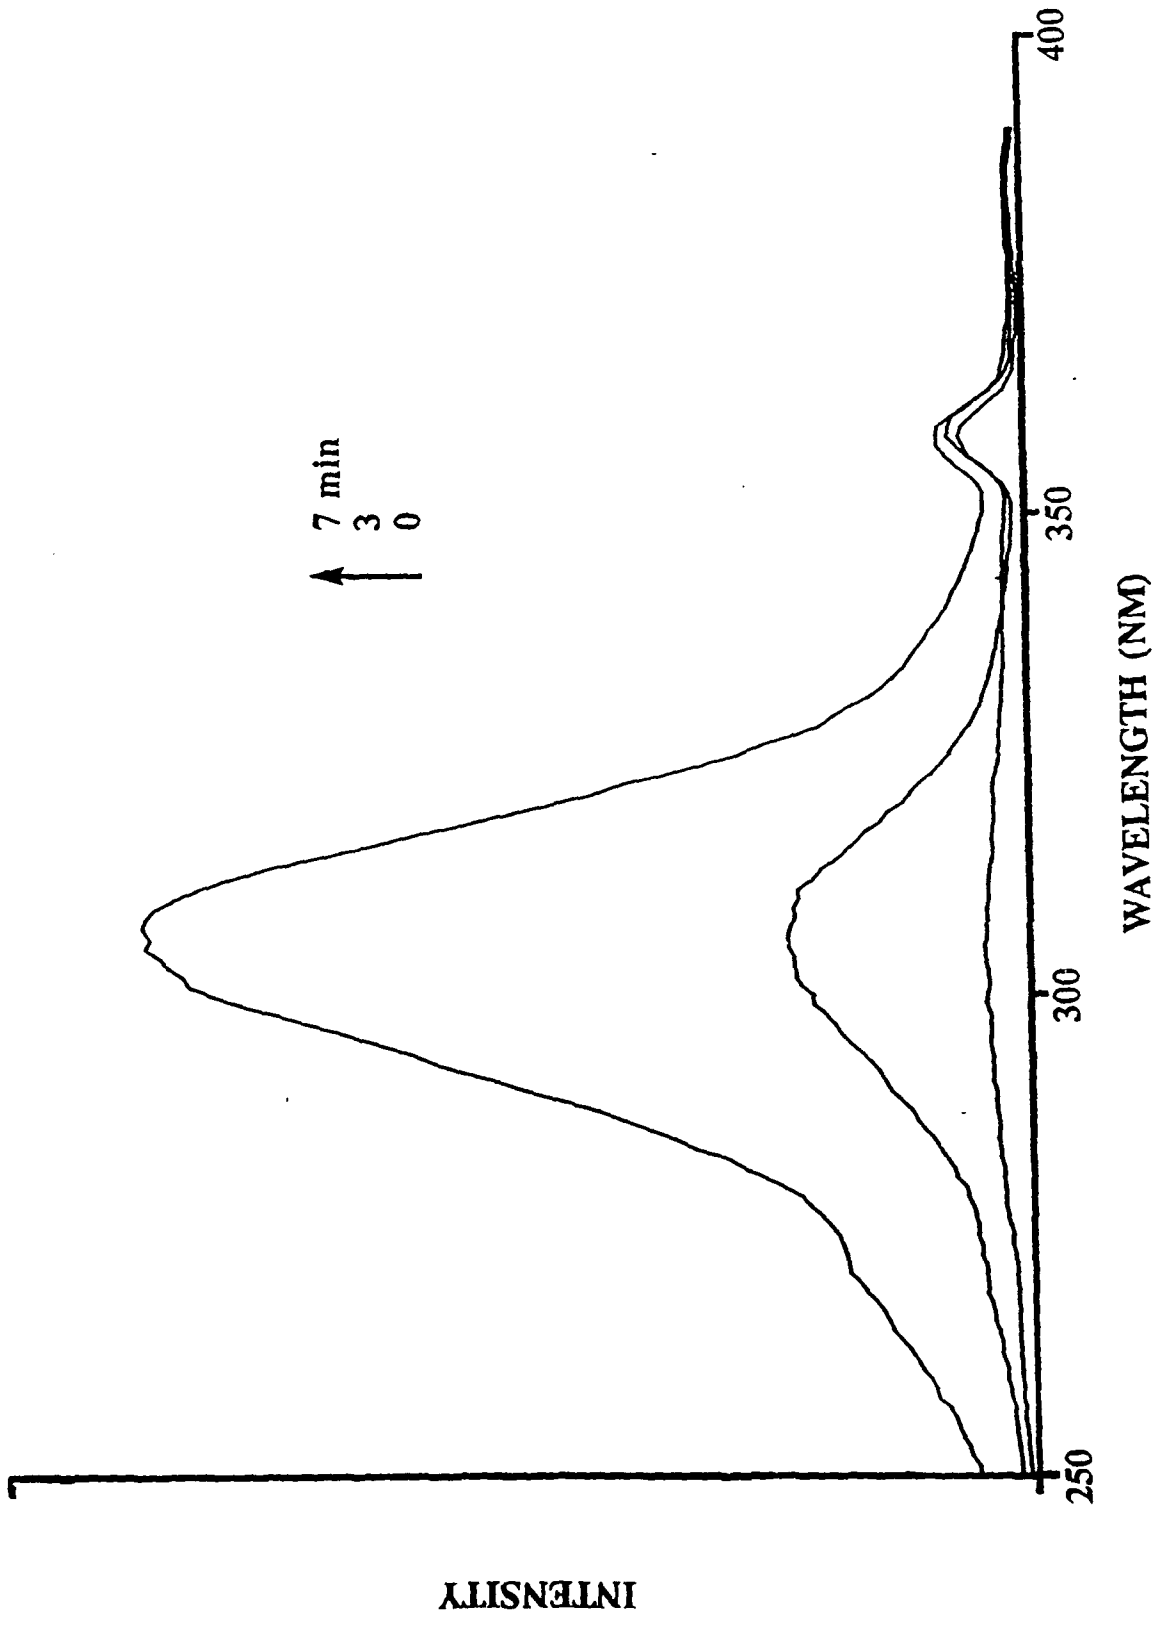

Fig. 10

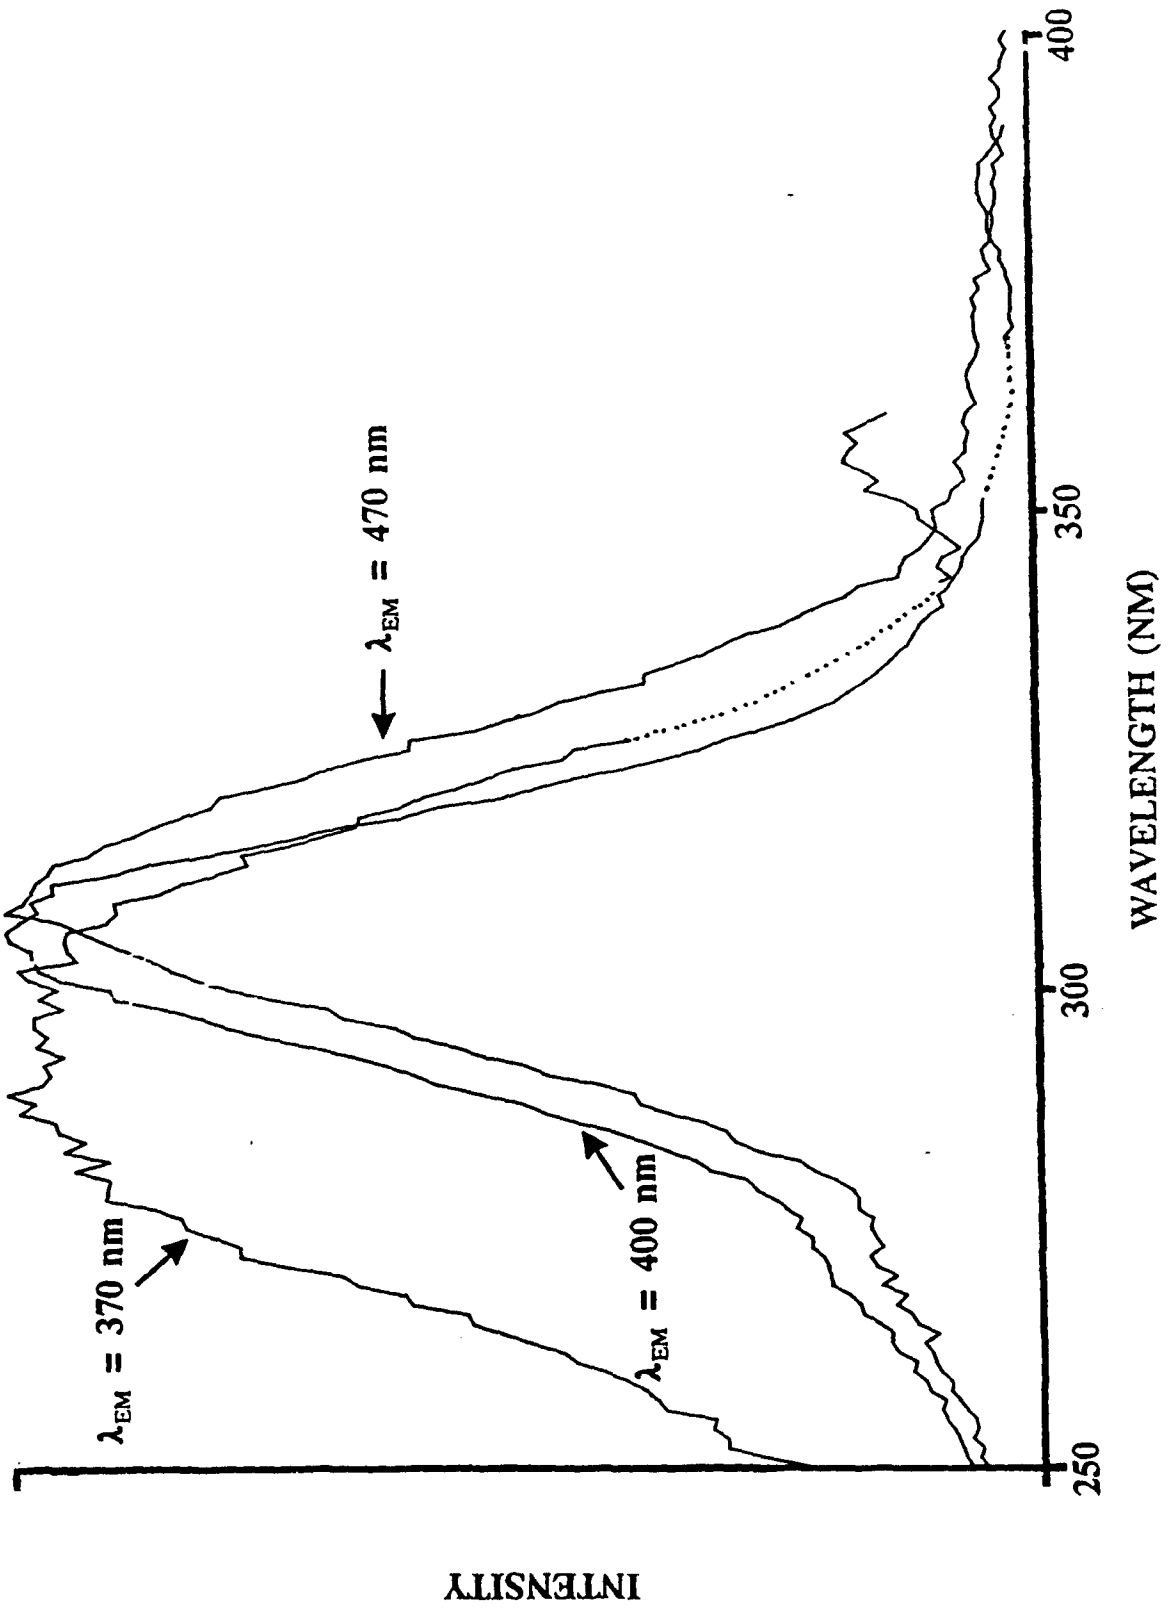
$\lambda_{EM}$ = 470 nm
$\lambda_{EM}$ = 400 nm
$\lambda_{EM}$ = 370 nm
250
300
350
400
WAVELENGTH (NM)
INTENSITY

Fig. 11

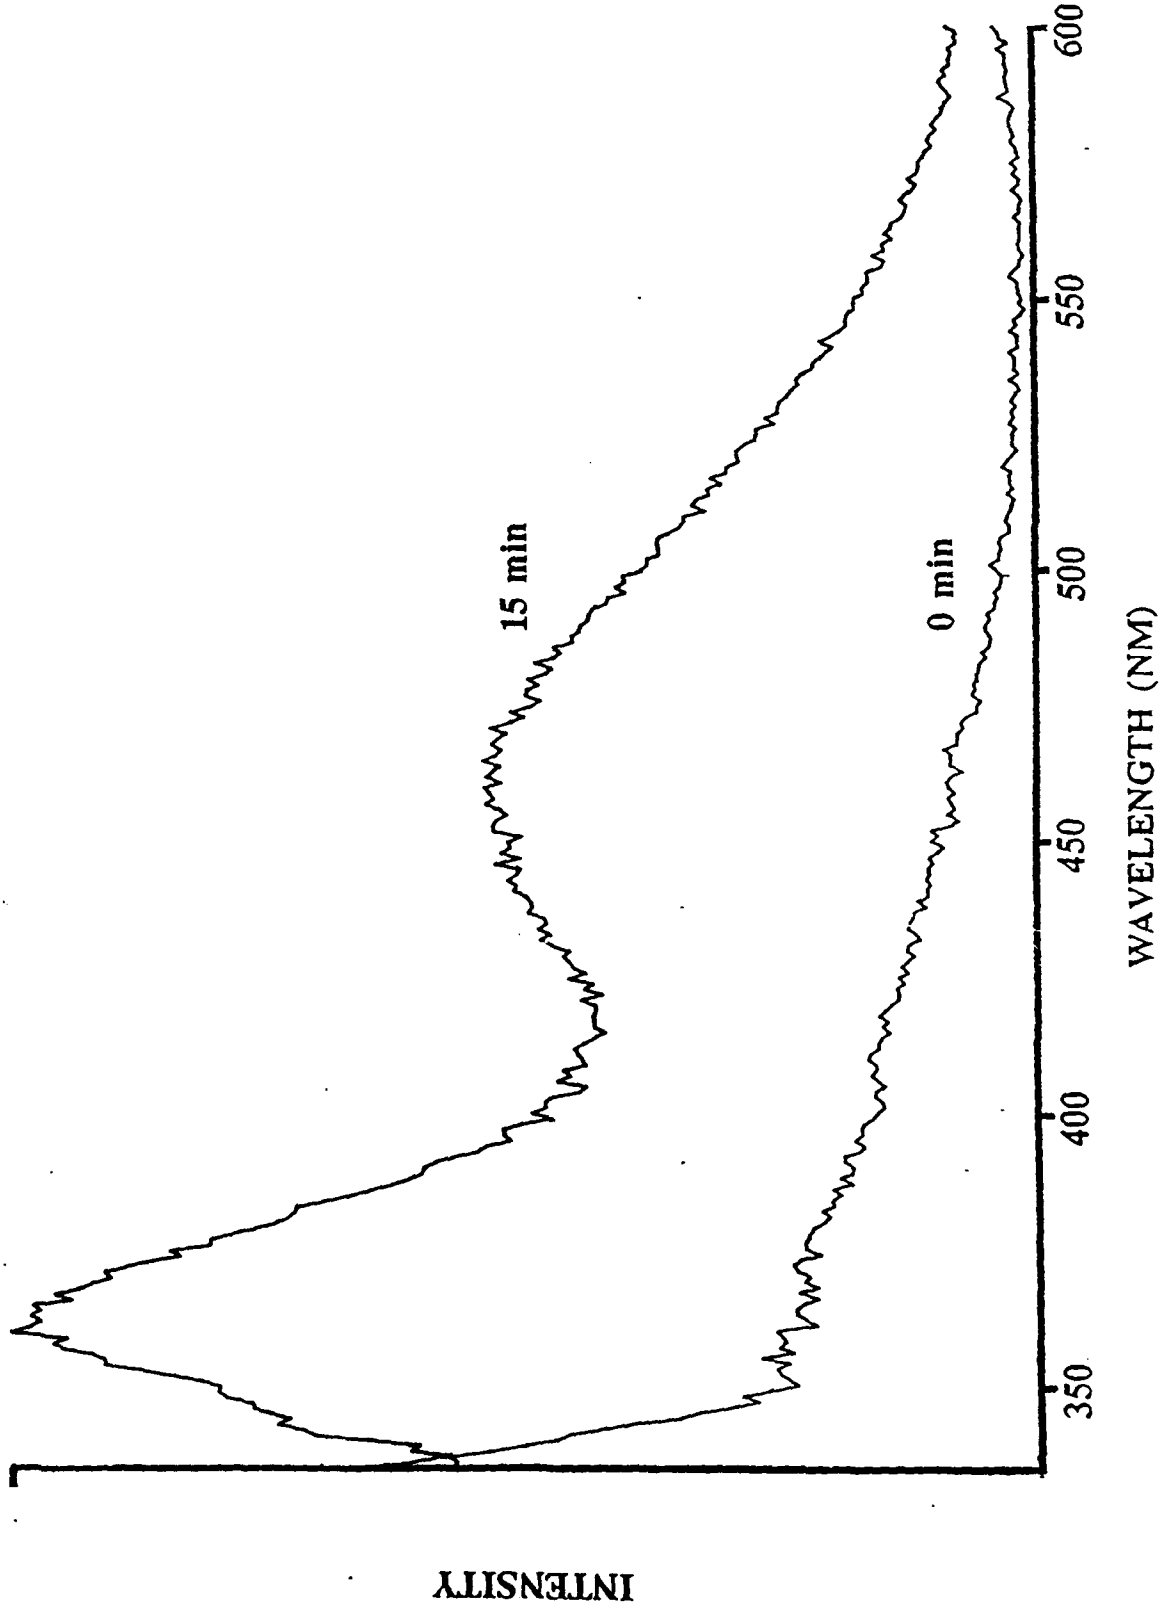

Fig. 12a

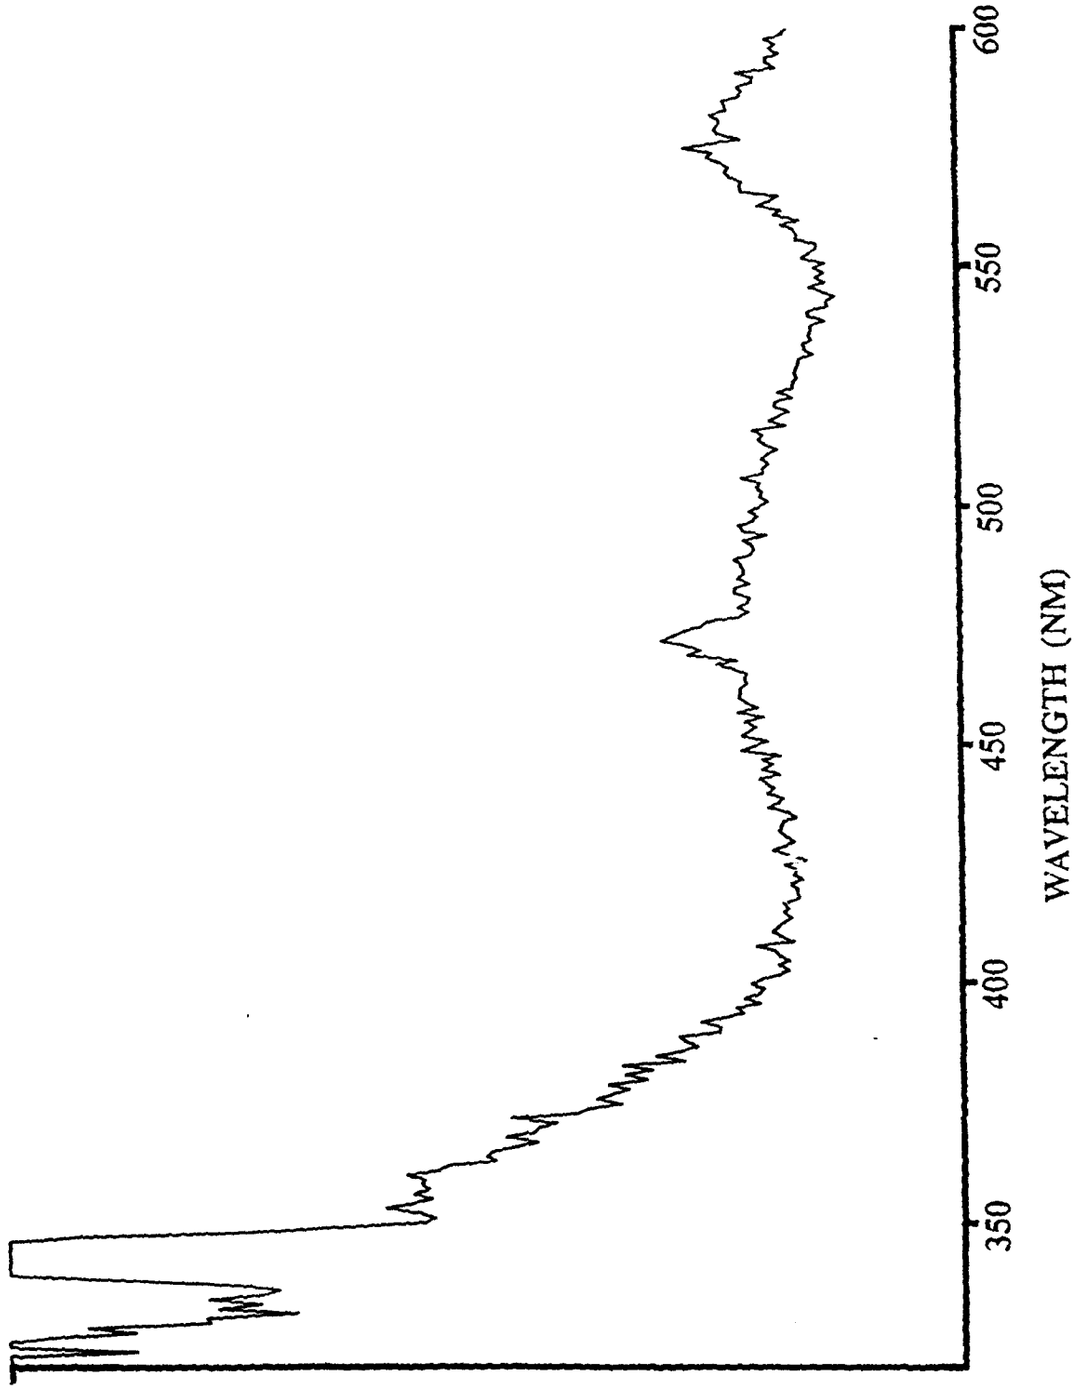

Fig. 12

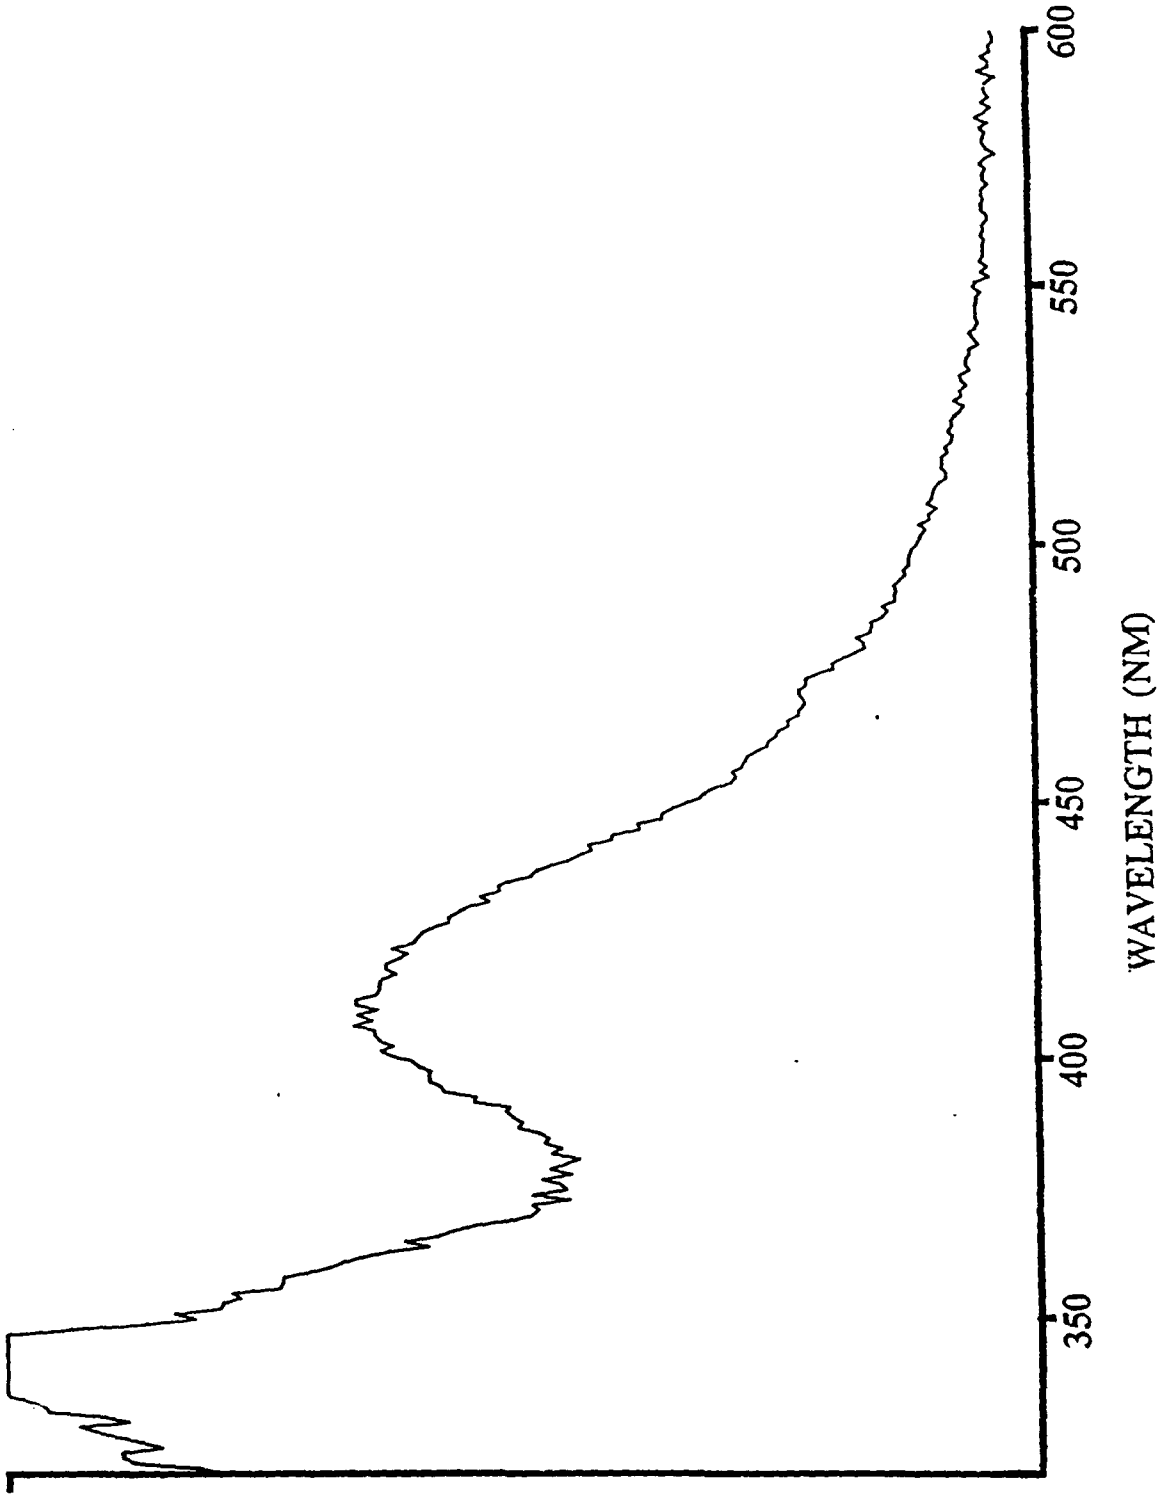

Fig. 13

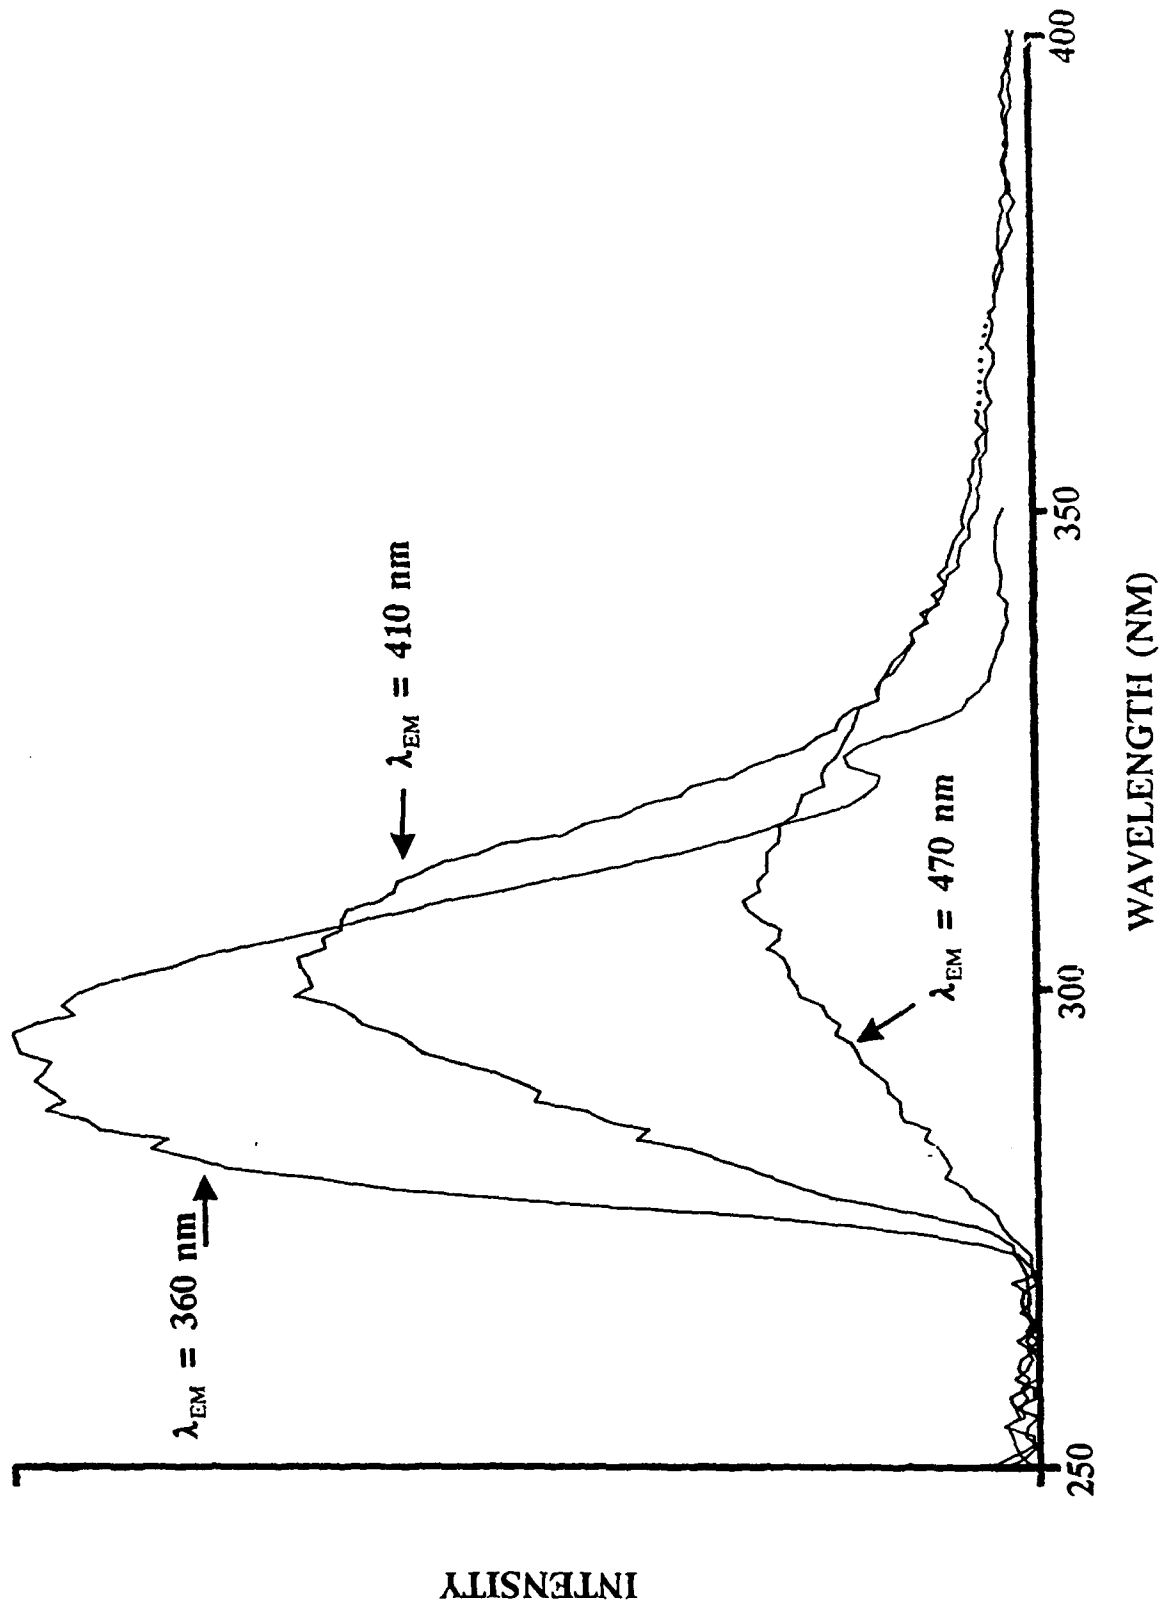
INTENSITY
250
300
350
400
WAVELENGTH (NM)
$\lambda_{EM}$ = 360 nm
$\lambda_{EM}$ = 410 nm
$\lambda_{EM}$ = 470 nm

Fig. 14

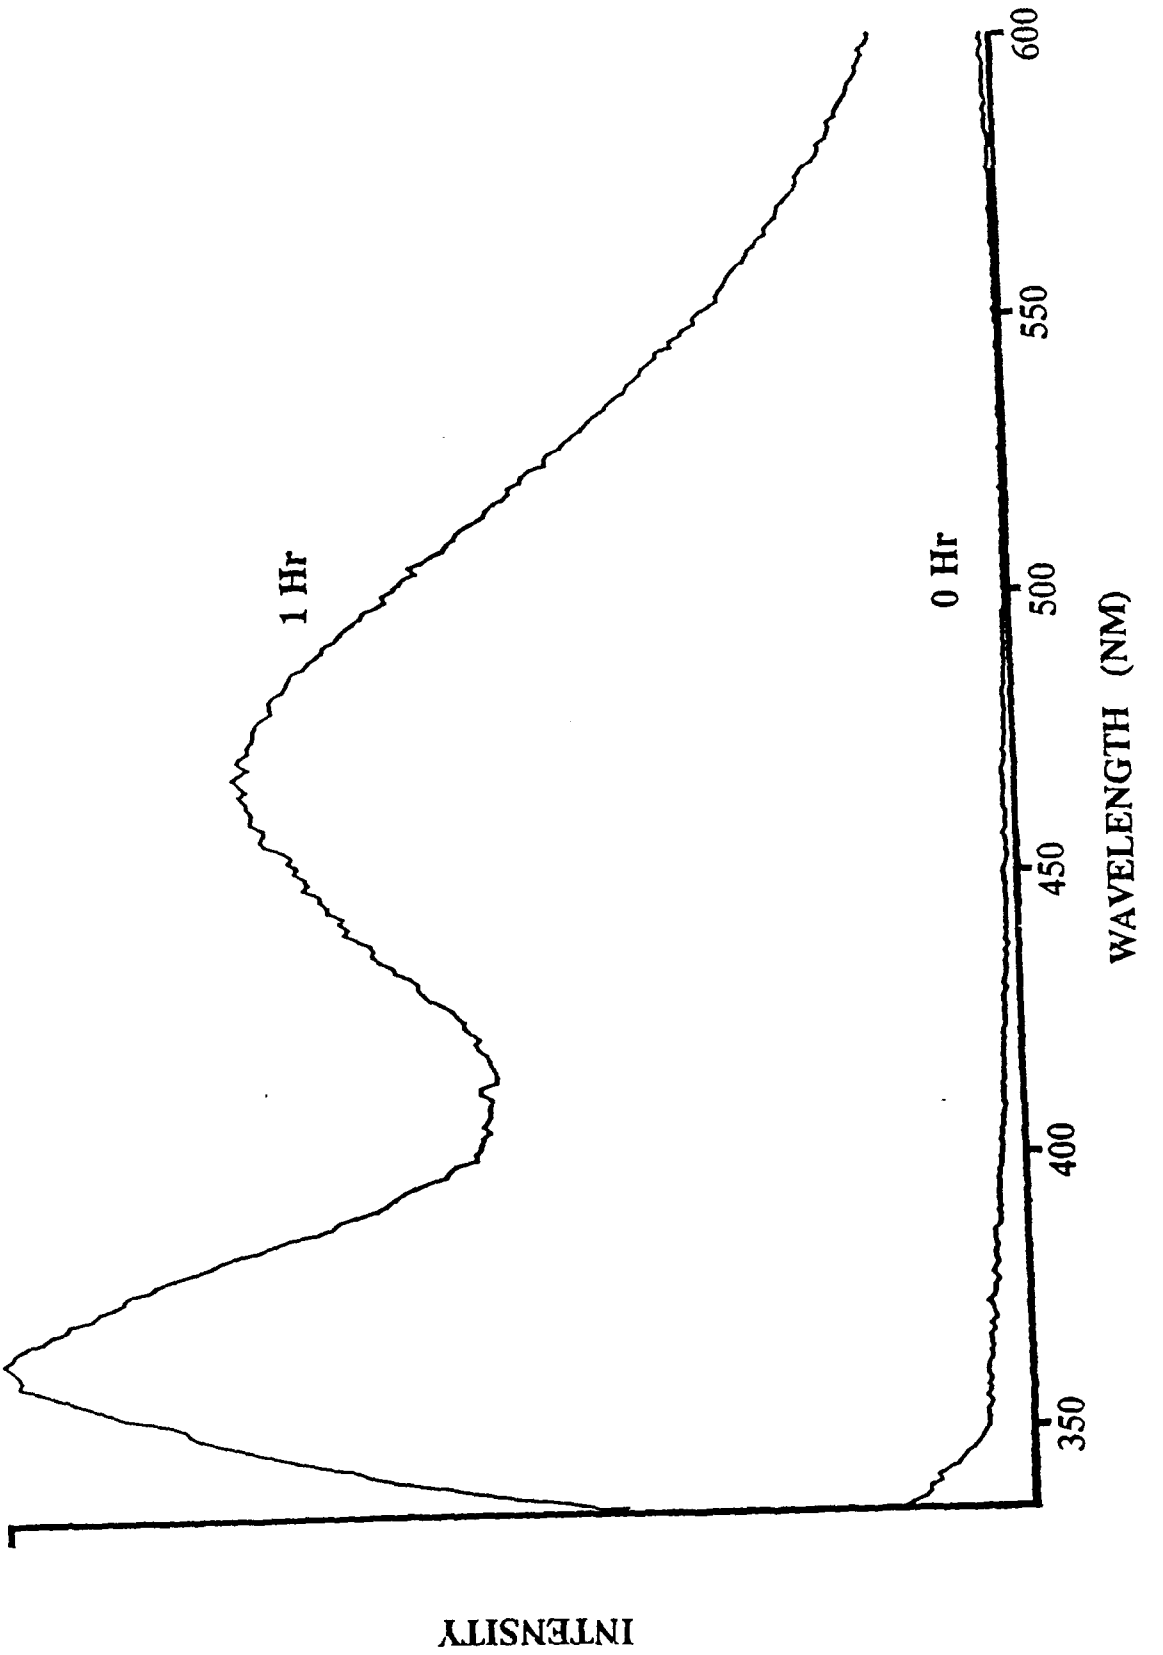

Fig. 15a

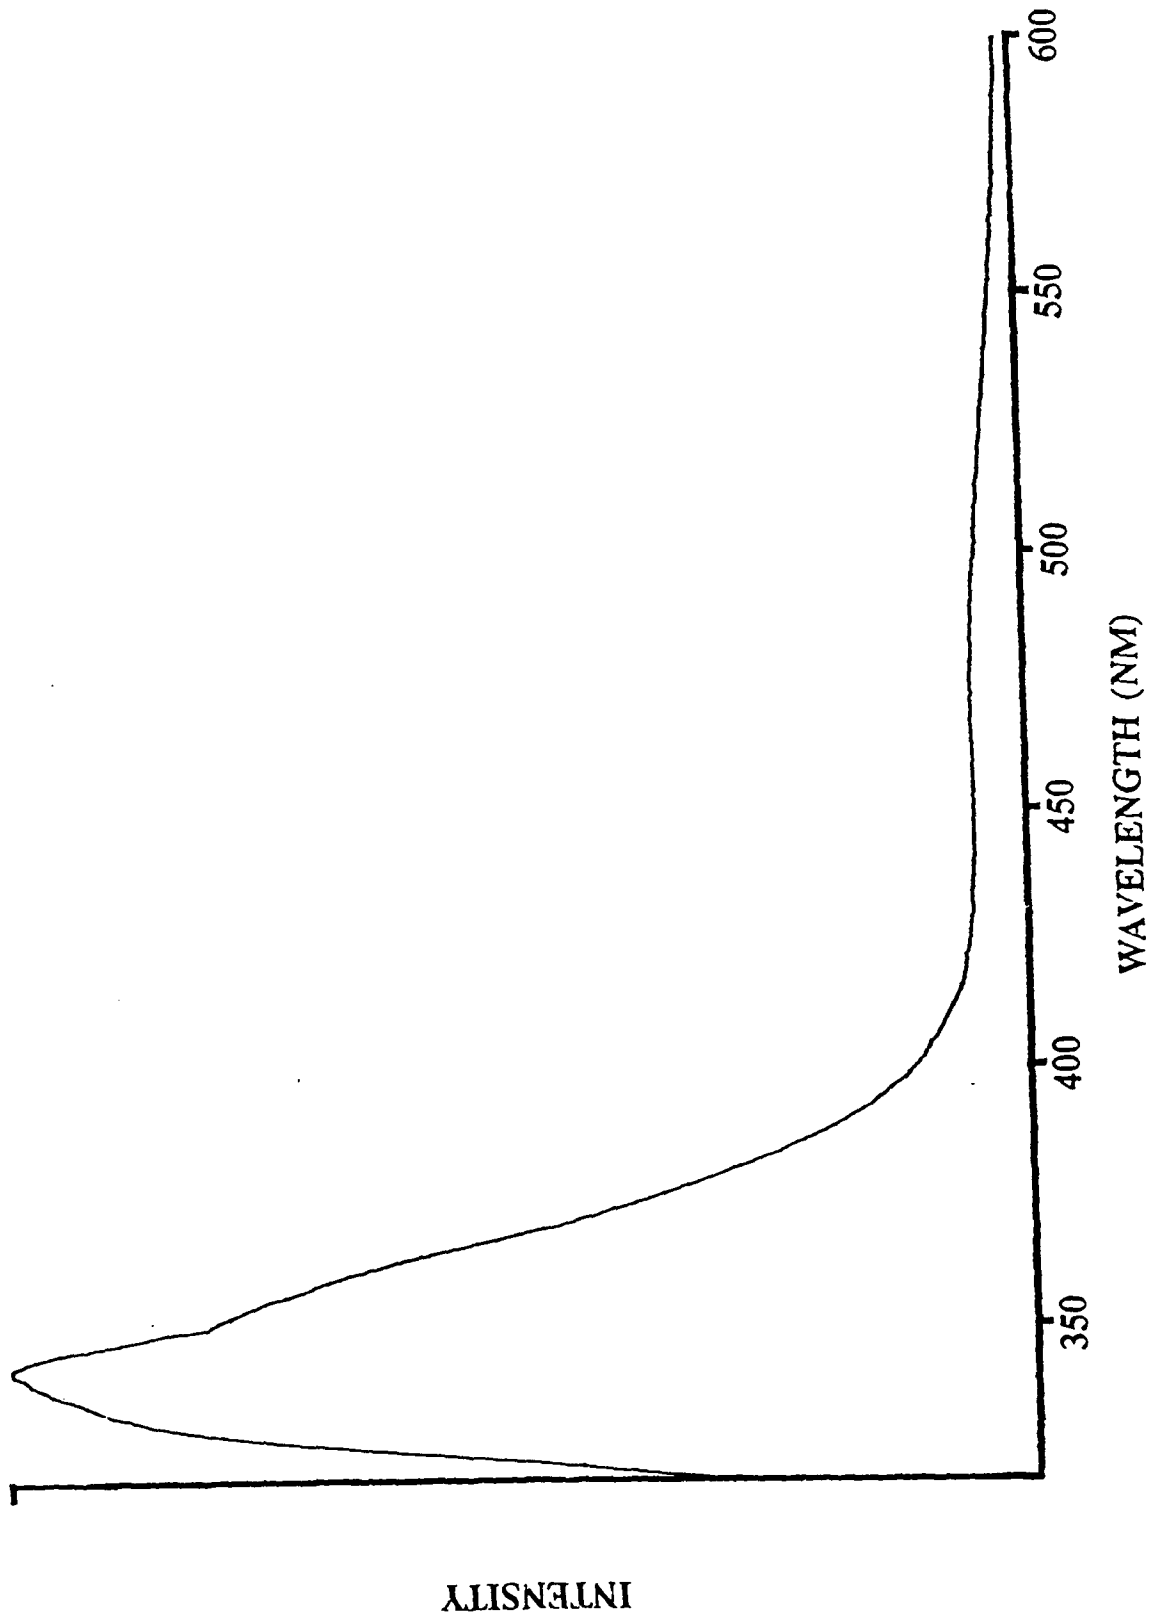

Fig. 15b

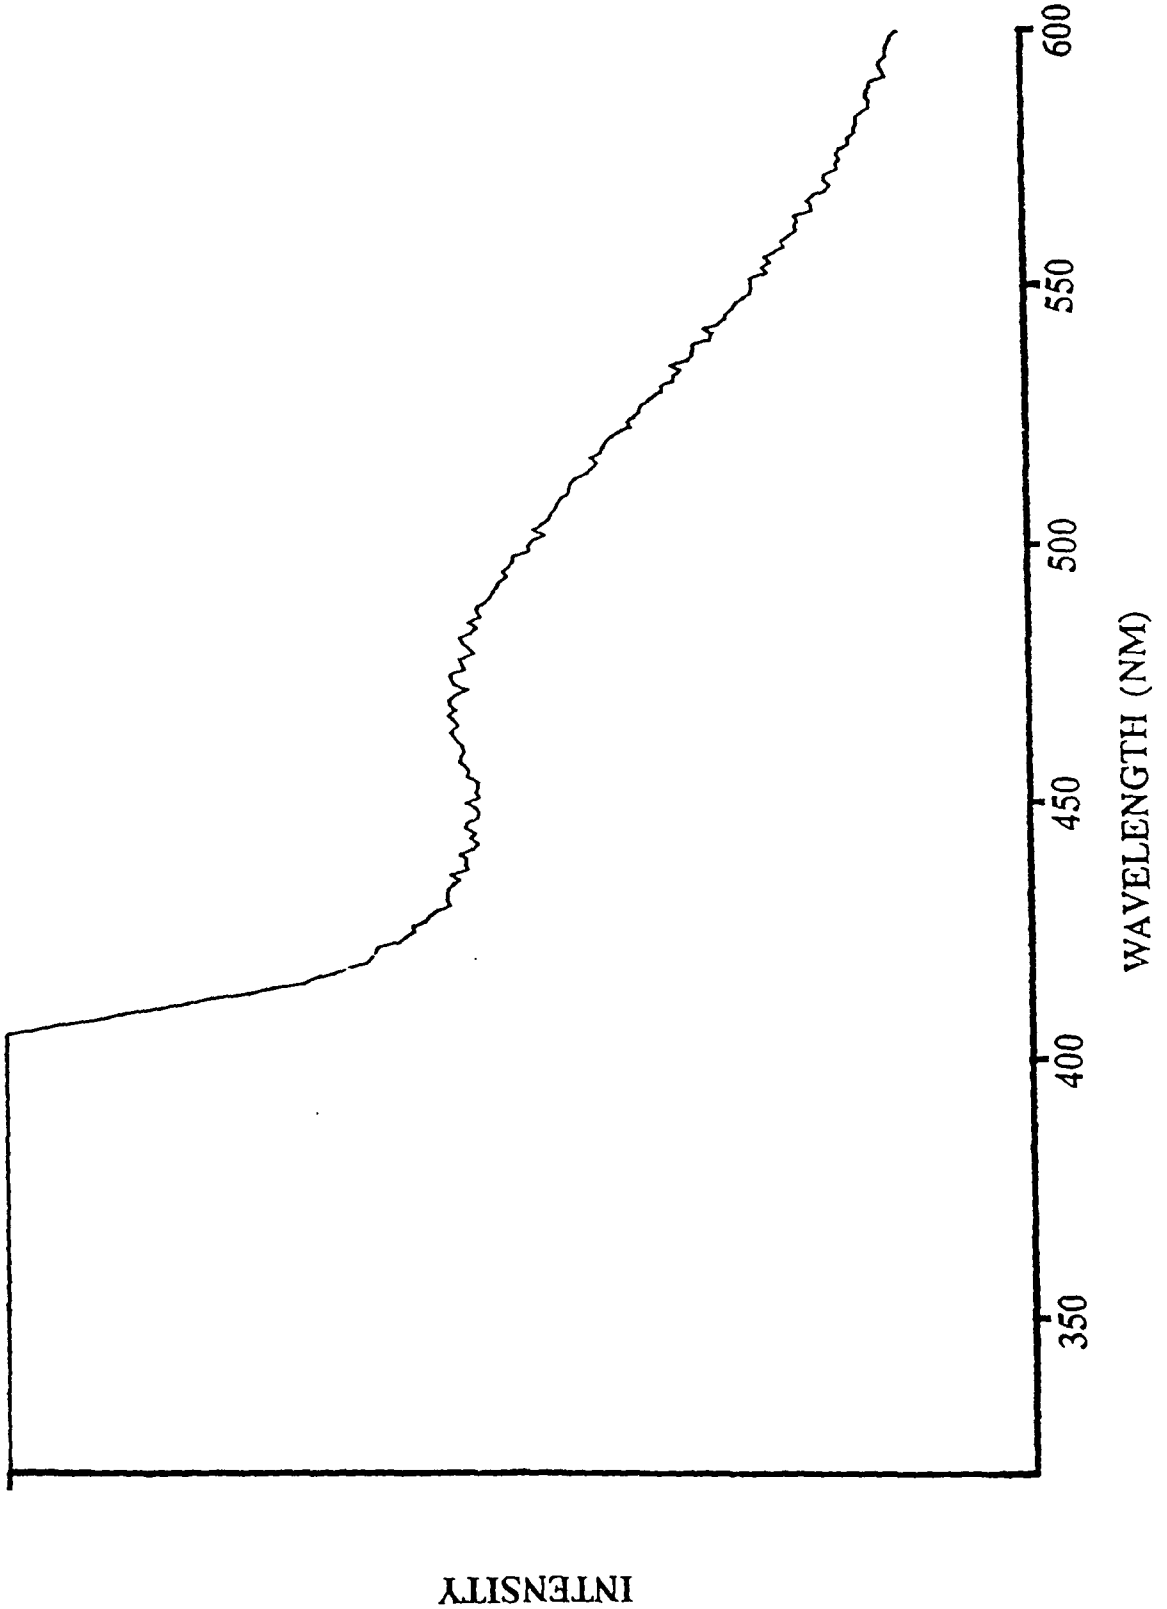

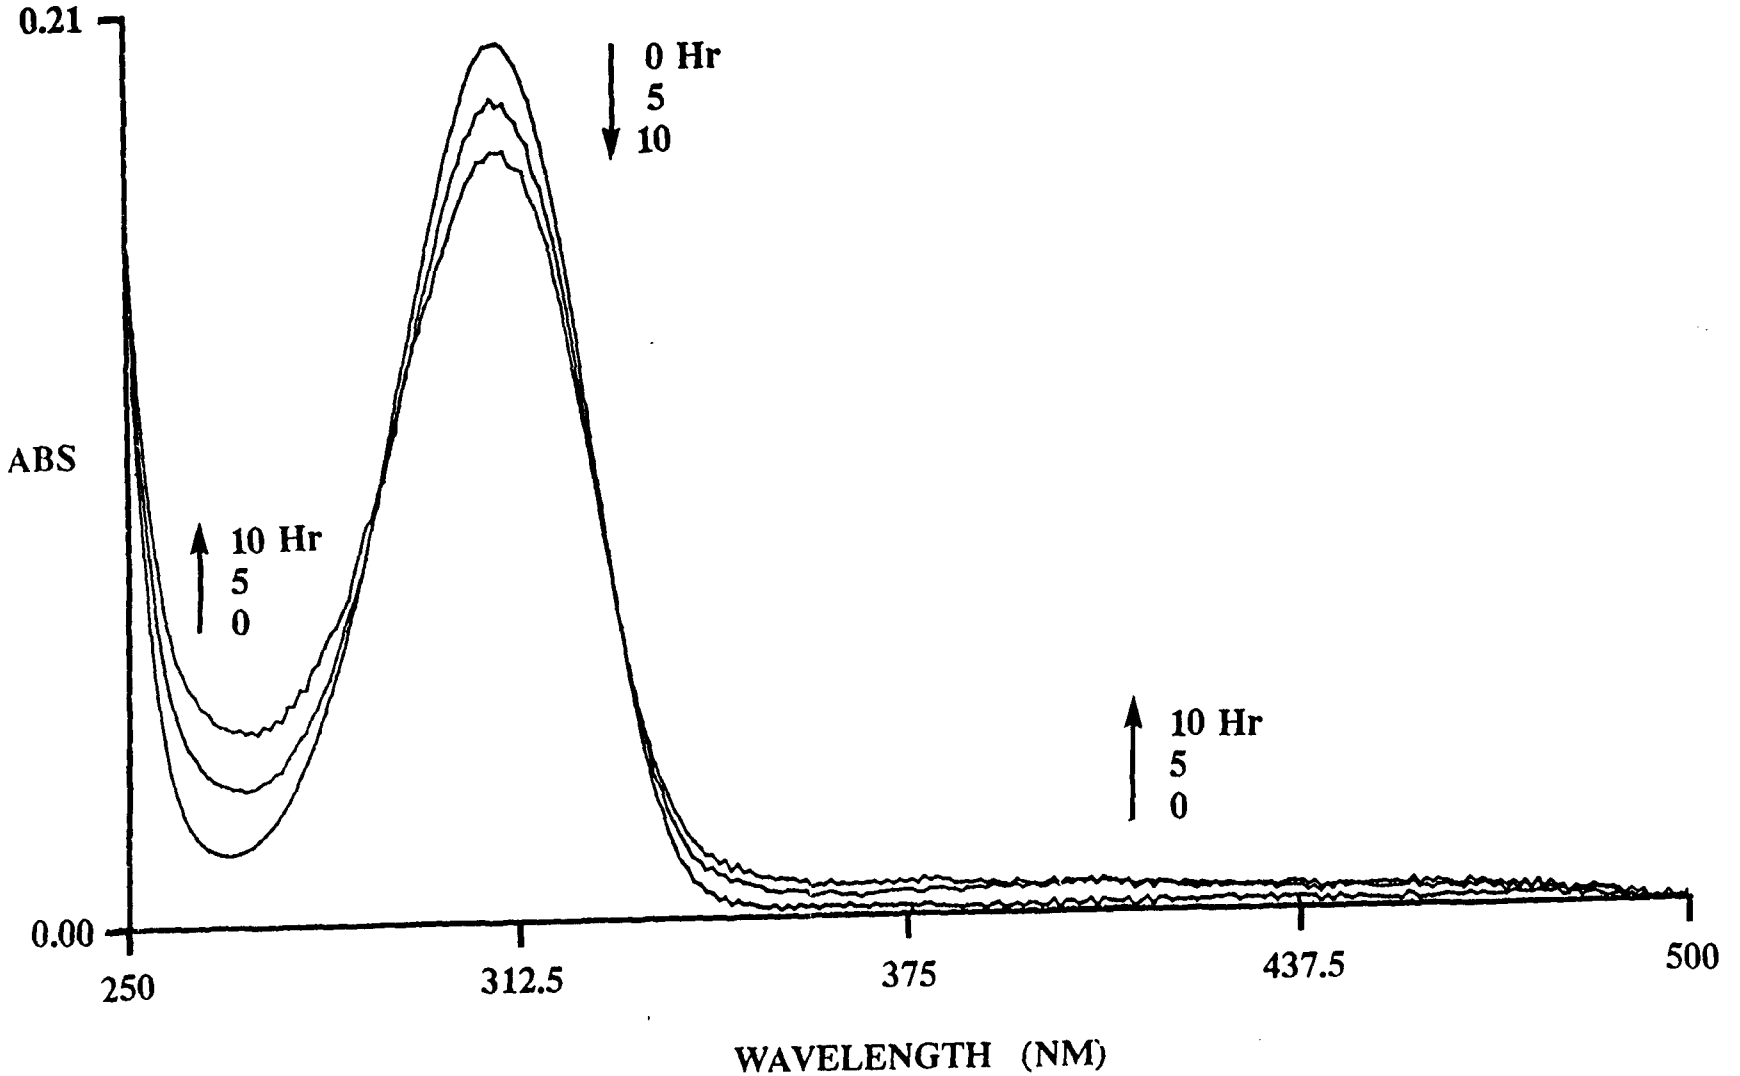
0.21
0.00
ABS
0 Hr
5
10
10 Hr
5
0
10 Hr
5
0
250
312.5
375
437.5
500
WAVELENGTH (NM)

Fig. 16

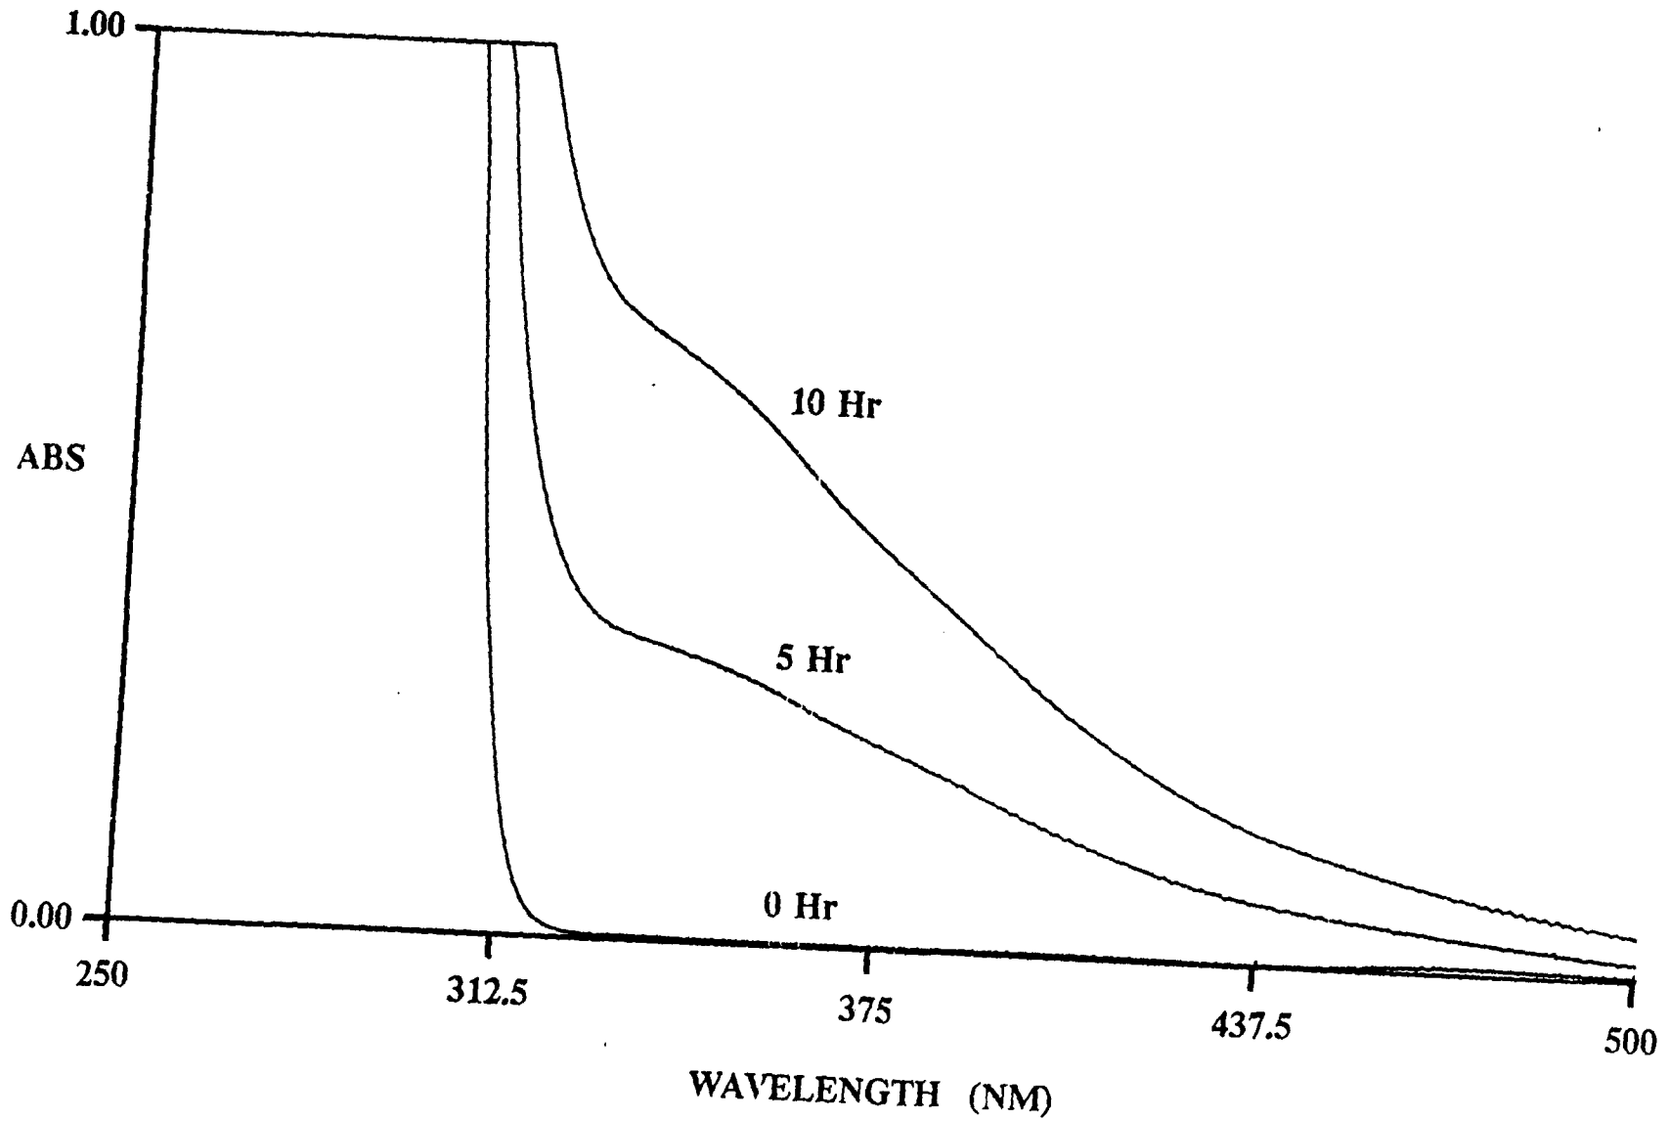


FIG. 17